



LIDCO, Pars SEE Zone, Assaluyeh,  
Integrated Methanol and Ammonia  
Plant 3000 MTPD MeOH / 900 MTPD NH3 PROJECT



NDE Procedure

Document No. 17735-15

Project No.	Vendor Doc.	P.O. No.	Department	Document Type	Serial No	Revision	Page
N278	VD	6019	GN	PRC	0016	01	Page 1 of 71

**Airpack B.V. - Air Compressor –  
Integrated Methanol and Ammonia Plant  
17735-COM NDE procedure (K020)**

NARGAN COMPANY	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: <i>M. Rezaei</i> DATE: 14/12/2023	
SIGN: <i>M. Rezaei</i>	

REV.	DATE	DESCRIPTION	DRAWN	CHECKED	APPROVED
01	14-12-2023	Issued for Approval	S.K.	S.K.	J.J.


NDE Procedure

Document No. 17735-15

Project No.	Vendor Doc.	P.O. No.	Department	Document Type	Serial No	Revision	Page
N278	VD	6019	GN	PRC	0016	01	Page 2 of 71

LIST OF REVISED PAGES

Rev. Page	01	02	03	04	05	Rev. Page	01	02	03	04	05	Rev. Page	01	02	03	04	05	Rev. Page	01	02	03	04	05	
1	X					26	X					51	X					76						
2	X					27	X					52	X					77						
3	X					28	X					53	X					78						
4	X					29	X					54	X					79						
5	X					30	X					55	X					80						
6	X					31	X					56	X					81						
7	X					32	X					57	X					82						
8	X					33	X					58	X					83						
9	X					34	X					59	X					84						
10	X					35	X					60	X					85						
11	X					36	X					61	X					86						
12	X					37	X					62	X					87						
13	X					38	X					63	X					88						
14	X					39	X					64	X					89						
15	X					40	X					65	X					90						
16	X					41	X					66	X					91						
17	X					42	X					67	X					92						
18	X					43	X					68	X					ATTACHMENT						
19	X					44	X					69	X					1						
20	X					45	X					70	X					2						
21	X					46	X					71	X					3						
22	X					47	X					72						4						
23	X					48	X					73						5						
24	X					49	X					74						6						
25	X					50	X					75						7						



NARGAN COMPANY	
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. BEZEL	DATE: 2023/05/23
SIGN:	

## INDEX



### PROCEDURE

	PAGE
MT – LIFTING LUGS	3
RT – PIPING	14

Please check whether ferrite content check (from page 66 till 71) is applicable here or not.

	NARGAN COMPANY
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

MT  
-  
LIFTING LUGS

	NARGAN COMPANY
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M.REZAEI DATE: 16 Dec 2023	
SIGN: 	

Doc Ref : MT 19108  
 Revision : 1  
 Date : 08-03-2022  
 Title : Magnetic testing procedure  
 Client : Airpack Nederland B.V.

## MAGNETIC TESTING PROCEDURE

Client : Airpack Nederland B.V.

Purpose of the examination : Magnetic particle inspection of welds.

Method : According to AWS D1.1 / D1.1M: 2015 (ASTM E709)

Issued by : Applus RTD BUA NL

Development – Revisions					
Revision no.	Prepared by	Date	Approved by	Date	Amendment details
1	Vincent Spieringhs	08-03-2022			Indicated in margin
0	Kevin Cocquyt	20-12-2019	Vincent Spieringhs	20-12-2019	

Date	08-03-2022	Date


Address  
 Delftweg 144, 3046 NC Rotterdam  
 P.O. Box 10065, 3004 AB Rotterdam  
 The Netherlands  
 www.ApplusRTD.com

<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

This publication is the intellectual property of Applus+ RTD and may not be used in whole or in part for any purpose other than the business of Applus+ RTD and may not be used for the business of the recipient and may not be passed to any other person without the permission of Applus+ RTD.

**Contents**

<b>1</b>	<b>Scope</b>	<b>3</b>
<b>2</b>	<b>Referenced documents</b>	<b>3</b>
2.1	<i>Applus+ RTD documents</i>	3
2.2	<i>Codes and standards</i>	3
2.3	<i>Abbreviations</i>	3
<b>3</b>	<b>General requirements</b>	<b>4</b>
3.1	<i>Personnel qualifications</i>	4
3.2	<i>Safety precautions</i>	4
3.3	<i>Surface preparation</i>	4
3.4	<i>Surface temperature</i>	4
3.5	<i>Identification and datum position</i>	5
3.6	<i>Viewing conditions</i>	5
<b>4</b>	<b>Equipment and consumables</b>	<b>5</b>
4.1	<i>Yokes</i>	5
4.2	<i>Light meters</i>	5
4.3	<i>Examination consumables</i>	5
<b>5</b>	<b>Examination</b>	<b>7</b>
5.1	<i>Examination method</i>	7
5.2	<i>Direction of magnetization</i>	7
5.3	<i>Extent of examination</i>	7
5.4	<i>Demagnetization</i>	7
5.5	<i>Post examination cleaning</i>	7
<b>6</b>	<b>Evaluation of indications</b>	<b>8</b>
<b>7</b>	<b>Acceptance standard</b>	<b>8</b>
7.1	<i>Choice of acceptance criteria</i>	8
7.2	<i>Acceptance criteria</i>	9
<b>8</b>	<b>Report</b>	<b>10</b>

NARGAN COMPANY	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec. 2023	
SIGN: 	

In the titel of document, MT is for lifting lugs and here for structural steel of skid. Vendor shall clarify this matter.

## 1 Scope

This procedure describes the method and acceptance criteria to be used for magnetic testing on structural steel skids with AC yoke magnetisation. To be performed in conformity with the requirements of;

- AWS D1.1/D1.1M:2015 (ASTM E709)

## 2 Referenced documents

Does it vendor's internal documents.

### 2.1 *Applus+ RTD documents*

NL-10	Written practice for the Training, Qualification, Certification and Authorization of NDT Personnel
CP 31201	Verification procedure for electric magnetic yokes
CP 31203	Verification procedure for magnetic particle suspensions
CP 31210	Verification procedure of light intensity meters

### 2.2 *Codes and standards*

ISO 9712	Qualification and certification of NDT personnel
SNT TC 1A: 2016	Personnel qualification and certification in NDT
AWS D1.1/D1.1M:2015 (ASTM E709)	Magnetic particle Examination
AWS D1.1/D1.1M:2015	Acceptance standard for magnetic particle examination

### 2.3 *Abbreviations*

AC	Alternating Current
HSE	Health Safety and Environment
kg	kilogram
MT	Magnetic Testing
NDE	Non Destructive Examination
CJP	Complete Joint Penetration
°C	Temperature in degree Celsius
mm	Millimetre
<	Less than
≥	Greater than or equal to
CJP	Complete joint penetration
NA	Not applicable

NARGAN COMPANY	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec. 2023	
SIGN: 	

### 3 General requirements

#### 3.1 Personnel qualifications

NDE - personnel shall be qualified and certified in accordance with the valid version of Applus+ RTD written practice, which is in conformity with the recommended practice SNT-TC-1A and ISO 9712, level MT 2 as minimum.

Shall have passed an eyesight examination within the past 12 months, according the ISO 9712 section 7.4 or equivalent.

#### 3.2 Safety precautions

All applicable HSE laws and regulations and the HSE rules of our customers shall be observed at all times. Furthermore Applus+ RTD develops its own HSE rules.

In case of conflict between rules and regulations, the strictest will prevail.  
Special consideration shall be given to:

- inflammable and/or volatile materials;
- contrast paint and aerosols as used in magnetic testing;
- Extra attention at magnetic testing on hot objects > 50°C.

Use of safety gloves and eye protection is recommended.

#### Note:

The vapors from the consumables may be hazardous. Proper ventilation shall be provided in the case of testing being performed in a confined space. At no time during examination, shall there be exposure to any naked flames or sparks due to the flammable nature of the materials.

The use of aerosol containers and dry powders in confined spaces is dangerous and therefore it is only permitted in accordance with the Applus+ RTD safety pocketbook "working in confined spaces".

#### 3.3 Surface preparation

Prior to the magnetic examination the surface or weld surface plus at least 25 mm on both sides of the weld, shall be dry and free of dirt, grease, coating, preserving, scale, welding flux, weld spatter, oil and other matter, that could obscure surface openings or otherwise interfere with the examination.

Typical cleaning agents which may be used are detergents, organic solvents, de-scaling solutions, and paint removers. Degreasing and ultrasonic cleaning methods may also be used.

Surface preparation by grinding or machining may be necessary where surface irregularities could mask indications or produce false indications.

#### 3.4 Surface temperature

The surface temperature of the part to be examined (only for the "wet method") shall be within the temperature range limitations set by the manufacturer of the particles.

##### 3.4.1 High temperature

If the (surface) temperature is > 50°C suitable consumables shall be used.

NARGAN COMPANY	
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI	DATE: 16 Dec. 2023
SIGN:	

### 3.5 Identification and datum position

The welds shall be identified in accordance with the client's requirements.

The marking of flaw indications on the tested component shall be considered necessary as the resultant indications found at the time of inspection cannot be considered permanent. The position of flaws shall be marked on the tested component by a method that will not affect the use of the component or prejudice any subsequent testing.

### 3.6 Viewing conditions

At all times during the examination with the non-fluorescent method, the light intensity at the surface to be examined shall be 1000 lux. as a minimum.

## 4 Equipment and consumables

### 4.1 Yokes

An AC magnet Yoke shall be used.

The lifting power shall be checked prior to examination, and shall be 4.5 kg as minimum at the maximum pole spacing that will be used.

The verification of the yoke shall be done once a year or whenever the yoke has been damaged or repaired, in accordance with procedure Applus+ RTD CP 31201.

A field indicator (e.g. Berthold field indicator) may be used, if necessary, to determine the field direction.

### 4.2 Light meters

Light meters shall be calibrated at least once a year (12 month period +/- 2 weeks) or whenever the meter has been repaired. If meters have not been in use for one year or more, calibration shall be done before being used.

The light meters have to be verified, according to Applus+ RTD verification procedure CP 31210.

### 4.3 Examination consumables

The examination consumables to be used must provide sufficient contrast with the surface to be examined. The examination medium shall be supplied by Applus+ RTD.

The preferred examination consumables are given on page 6; other products may be used after approval by Applus+ RTD level 3 specialist.

	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec. 2023	
SIGN: 	

### 4.3.1 Black particles (wet method)

The magnetic particles, black and fluorescent, to be used in the examination shall meet the following requirements:

- Are oil or water suspended;
- The colour of the particles shall be such as to provide an adequate contrast with the surface being examined;
- The examination consumables shall be agitated (shaken) properly, as per manufacturers' recommendation, to ensure that the dispersion of particles is equal throughout the entire use of the containers contents.
- The test medium shall be applied by either flowing or spraying over the surface. The force of the application shall be such that weakly formed indications are not disturbed or removed.

Wet particles: MR Chemie:

Type	Product	Temp. range	Suspension
• MR 76 SAS	Magnetic testink (black)	+5° to +50°C	Oil based
• MR 221 GF	Magnetic testink (black)	+5° to +50°C	Water based

These wet particles have been tested by the manufacturer for conformity. Where necessary the examination medium will be tested in accordance with verification procedure Applus+ RTD CP 31203.

### 4.3.2 Contrast paint

If the contrast between the surface and the examination medium is too low, a very thin contrast paint layer shall be applied to the surface.

The preferred contrast paint is given below; other contrast paint may be used after approval by Applus+ RTD level 3 specialist.

Type	Product	Temp. range	Suspension
• MR 72	White contrast paint	+5° to +50°C	
• MR 721	White contrast paint	+5° to +50°C	Water based

NARGAN COMPANY	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec. 2023	
SIGN: 	


## 5 Examination

### 5.1 Examination method


The magnetic particles used in an examination (wet or dry) shall be applied by the continuous method: The magnetizing current shall remain on while the examination medium is being applied and while excess of the examination medium will flow away, or the dry powder will be softly blown away. Following this, time shall be allowed for indications to form before removal of the magnetic field.

### 5.2 Direction of magnetization

To ensure detection of imperfections in all orientations, the area shall be magnetized in two directions approximately perpendicular to each other.

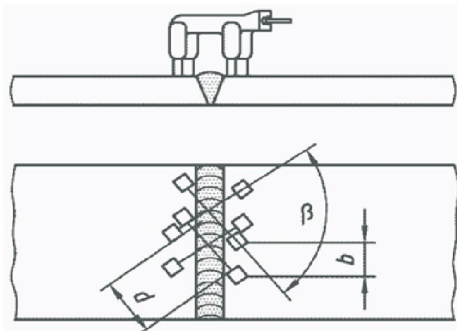

$$d \geq 75, b \leq 2d \text{ and } \beta = 90^\circ$$

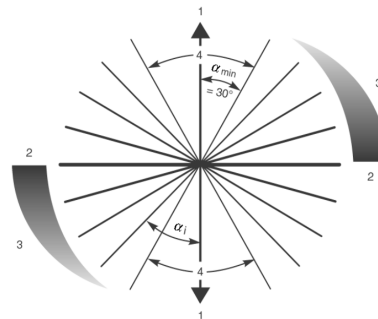

$\alpha$  = is the angle between the magnetic field and the direction of the imperfection  
 $\alpha_{min}$  = is the minimum angle for imperfection detection.  
 $\alpha_i$  = is an example of imperfection orientation.

1 = magnetic field direction, 2 = optimum sensitivity, 3 = reducing sensitivity and 4 = insufficient sensitivity

### 5.3 Extent of examination

The examination has to be executed in such a manner that there is sufficient overlap to ensure that 100% examination has been executed.

### 5.4 Demagnetization

The examined areas shall not be demagnetized after examination.

After testing with AC current, residual magnetization will normally be low and generally there is no need for demagnetization of the tested object.

### 5.5 Post examination cleaning

The examined areas shall not be cleaned after examination.

NARGAN COMPANY	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec. 2023	
SIGN:	

## 6 Evaluation of indications

The evaluation of indications shall be done during the magnetization.

An indication of an imperfection may be larger than the real imperfection. However the size of the indication will be the basis for the evaluation.

A linear indication is an indication (piping porosity), of which the length is larger than 3 times the width.

A rounded (non-linear) indication (porosity) is an indication of circular- and/or elliptical shape with a length equal to or less than 3 times its width.

**Note:**

Not all of the indications are relevant, because excessive surface roughness, etc. may cause similar indications. Any questionable indications shall be re-examined, possibly after surface improvement, to determine whether or not it is relevant.

## 7 Acceptance standard

### 7.1 Choice of acceptance criteria

The client shall provide the load condition and load direction before examination.

Required info:

Statically loaded or cyclically loaded.

Tensile stress during any load condition: Yes or No.

When the load condition is unknown the used acceptance shall be cyclically loaded with tensile stress.

	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec. 2023	
SIGN: 	

## 7.2 Acceptance criteria

Acceptance according AWS D1.1: 2015 Claus 6. Table 6.1 and Clause 9, Table 9.6.

Discontinuity Category and Inspection Criteria	Table 6.1		Table 9.6
	Statically Loaded Nontubular Connections	Cyclically Loaded Nontubular Connections	Tubular Connections (All Loads)
1) Crack Prohibition <i>Any crack shall be unacceptable, regardless of size or location.</i>	x	x	x
(2) Weld/Base Metal Fusion <i>Complete fusion shall exist between adjacent layers of weld metal and between weld metal and base metal.</i>	x	x	x
(7) Undercut <i>A) For material less than 1 in [25 mm] thick, undercut shall not exceed 1/32 in [1 mm], with the following exception: undercut shall not exceed 1/16 in [2 mm] for any accumulated length up to 2 in [50 mm] in any 12 in [300 mm]. For material equal to or greater than 1 in [25 mm] thick, undercut shall not exceed 1/16 in [2 mm] for any length of weld.</i> <i>(B) In primary members, undercut shall be no more than 0.01 in [0.25 mm] deep when the weld is transverse to tensile stress under any design loading condition. Undercut shall be no more than 1/32 in [1 mm] deep for all other cases.</i>	x	NA	NA
(8) Porosity <i>(A) CJP groove welds in butt joints transverse to the direction of computed tensile stress shall have no visible piping porosity. For all other groove welds and for fillet welds, the sum of the visible piping porosity 1/32 in [1 mm] or greater in diameter shall not exceed 3/8 in [10 mm] in any linear inch of weld and shall not exceed 3/4 in [20 mm] in any 12 in [300 mm] length of weld.</i> <i>(B) The frequency of piping porosity in fillet welds shall not exceed one in each 4 in [100 mm] of weld length and the maximum diameter shall not exceed 3/32 in [2.5 mm]. Exception: for fillet welds connecting stiffeners to web, the sum of the diameters of piping porosity shall not exceed 3/8 in [10 mm] in any linear inch of weld and shall not exceed 3/4 in [20 mm] in any 12 in [300 mm] length of weld.</i> <i>(C) CJP groove welds in butt joints transverse to the direction of computed tensile stress shall have no piping porosity. For all other groove welds, the frequency of piping porosity shall not exceed one in 4 in [100 mm] of length and the maximum diameter shall not exceed 3/32 in [2.5 mm].</i>	x	NA	NA
	NA	x	x
	NA	x	x

NARGAN COMPANY	
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI	DATE: 16 Dec 2023
SIGN:	

**Discontinuities 3, 4, 5 and 6 shall only be subject to visual inspection.**

**Discontinuities 2, 7 and 8 shall only be evaluated on length in case of an MPI indication and shall not be evaluated on other dimensions.**


**X shall be evaluated**

**NA shall not be evaluated**



## 8 Report

For each magnetic examination carried out a report shall be written. Each report shall contain the following information as minimum:

- Procedure number and revision;
- Examination standard, acceptance standard;
- Client;
- Date of examination;
- Equipment used and type of current;
- Magnetic particles used incl. batch numbers ( wet or dry);
- Object data and examined parts;
  - base material;
  - extent of examination
  - in case of welds type of weld, welding process and filler material;
  - heat treatment (if applicable);
  - thickness;
  - temperature of the object;
- Viewing conditions(light intensity);
- Drawing or record of all indications exceeding the acceptance standard;
  - All relevant indications shall be reported with as minimum the type, location and extent (length, diameter or aligned);
- Name operator(s) qualification and signature operator(s) who performed examination.

 NARGAN COMPANY	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec. 2023	
SIGN: 	

# RT - PIPING

	NARGAN COMPANY
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M.REZAEI DATE: 16 Dec 2023	
SIGN: 	

Doc Ref : 2022 0021  
 Revision : 00  
 Date : 15-03-2022  
 Title : Radiographic Examination Procedure B.V.  
 Client : Airpack Netherlands



## RADIOGRAPHIC EXAMINATION PROCEDURE

This procedure describes the method for radiographic examination on piping welds.

Client : Airpack Netherlands B.V.  
 Project : MMPS Gas Compression project (MGCP)  
 RAMZ Project ID : SOM000MM0612-AA

The examination will be performed in accordance with the requirements of:

**ASME BPVC Section V, article 2, edition 2021**

This procedure shall only be used in conjunction with the following standard Applus+ technical procedures:

RT 21002 revision 29

Development – Revisions					
Revision No.	Prepared By	Date	Approved By	Date	Amendment Details
00	VMJ.Spieringhs	15-03-2022			
VMJ Spieringhs RT3 ISO 9712/N43899 2022.03.15 11:15:52 +01'00'					
Date:	15-03-2022	Date:		Date:	

Address  
 Delftweg 144, 3046 NC Rotterdam  
 P.O. Box 10065, 3004 AB Rotterdam  
 The Netherlands  
[www.ApplusRTD.com](http://www.ApplusRTD.com)



<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN:	

This publication is the intellectual property of Applus+ and may not be used in whole or in part for any purpose other than the business of Applus+ and may not be used for the business of the recipient and may not be passed to any other person without the permission of Applus+.

Doc Ref : 2022 0021  
Revision : 00  
Date : 15-03-2022  
Title : Radiographic Examination Procedure B.V.  
Client : Airpack Netherlands

## Revision History



Revision Number	Date	Section	Brief Description of change	Author of Change
0	15-03-2022		Issued as new document	VMJ.Spieringhs

	NARGAN COMPANY
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M.REZAEI DATE: 16-Dec-2023	
SIGN: 	

Doc Ref : 2022 0021  
Revision : 00  
Date : 15-03-2022  
Title : Radiographic Examination Procedure B.V.  
Client : Airpack Netherlands

## Contents

<b>1</b>	<b>Scope .....</b>	<b>4</b>
5.2	<i>Films</i> .....	4

	NARGAN COMPANY
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M.REZAEI DATE: 16 Dec 2022	
SIGN: 	

## 1 Scope

This procedure describes the amendments to the following standard Applus+ technical procedure:

- RT 21002 revision 29



### *Amendments to the following paragraphs of standard procedure RT 21002*

#### 5.2 Films

The films to be used shall be in accordance to the ISO 11699-1, class C5 (e.g. Agfa D7) or better. For wall thicknesses  $\leq 15\text{mm}$  class C3 (e.g. Agfa D4) films are recommended.

The films must be free of defects that disturb the evaluation of the results of the radiographic examination. The following disturbances are also unacceptable:

- Repairs carried out on films due to improper treatment or development.
- Scratches and contamination.
- Static discharge.
- Indications of defect screens or carrier errors.

	NARGAN COMPANY
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M.REZAEI DATE: 16 Dec 2022	
SIGN: 	

Doc Ref : RT 21002  
 Revision : 29  
 Date : 16-12-2021  
 Title : Radiographic examination  
 Type : Standard procedure




## RADIOGRAPHIC EXAMINATION PROCEDURE

### Radiographic Examination of welds and materials including castings in metallic materials up to 75 mm.


To be performed in conformity with the requirements of:

**ASME BPVC Section V, article 2, edition 2021**

Development – Revisions					
Revision No.	Prepared By	Date	Approved By	Date	Amendment Details
29	T. Cornelissen	16-12-2021	T. Speelmeijer	16-12-2021	
28		17-12-2019		17-12-2019	
0		01-08-1991			


 Digitally signed  
 by Theo  
 Cornelissen  
 Date: 2021.12.17  
 08:45:57 +01'00'

Theo Speelmeijer  
 MT3 PT3 RT3 UT3  
*Theo Speelmeijer*

 NARGAN COMPANY	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023 SIGN: <i>m. rezaei</i>	



Date: 16-12-2021      Date: 16-12-2021      Date:  
 Address  
 Delftweg 144, 3046 NC Rotterdam  
 P.O. Box 10065, 3004 AB Rotterdam  
 The Netherlands  
[www.ApplusRTD.com](http://www.ApplusRTD.com)

This publication is the intellectual property of Applus+ and may not be used in whole or in part for any purpose other than the business of Applus+ and may not be used for the business of the recipient and may not be passed to any other person without the permission of Applus+.



Doc Ref : RT 21002  
Revision : 29  
Date : 16-12-2021  
Title : Radiographic examination  
Type : Standard procedure

## Revision History

Revision Number	Date	Section	Brief Description of change	Author of Change
0	01-08-1991		Issued as new document	
10	18-10-2001	5.1		A. Kuiper
11	17-03-2003		Addenda 2002 updated	H. Luykx
12	09-07-2003		Se75 added	H. Luykx
13	03-02-2004	2.1	Addenda A03 updated	P. Briggeman
14	03-02-2005		Updated to edition 2004	
15	30-08-2006		Updated to edition 2004 including addenda 2005	P. Briggeman
16	11-01-2007		Updated to edition 2004 including addenda 2006	P. Briggeman
17	20-09-2007		Updated to ASME BPV edition 2007	P. Briggeman
18				
19	20-10-2009		Revised to addenda 2009	P. Briggeman
20	14-12-2010		Revised to edition 2010	R. Penders
21	15-12-2011		Revised to edition 2011	R. Penders
22	01-06-2012	2.1		R.A. Coenen
23	10-09-2013	2.1, 2.3.1, 2.5, 3.2, 3.3, 3.4, 3.5, 4.5, 5.1, 7		P. Briggeman
24	05-05-2014	2.1, 2.7, 3.6, 4.5.2,		P. Briggeman
25	25-10-2015		Updated to edition 2015	P. Briggeman
26	25-02-2016	8		P. Briggeman
27	12-12-2017	3.5, 5.5,	Updated to edition 2015	P. Briggeman
28	17-12-2019		Complete revised and updated to ASME BPVC code V, 2019.	M. Vondenhoff
29	16-12-2021	1, 2, 4, 5.1, 5.3, 6.1, 6.2, 6.6, 6.8, 6.11	Updated to the ASME BPVC section V 2021 edition and amended castings	T. Speelmeijer

	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

<b>Contents1</b>	<b>Scope</b>	<b>4</b>
<b>2</b>	<b>References and abbreviations</b>	<b>4</b>
2.1	<i>Applus+ documents</i>	4
2.2	<i>Codes and standards</i>	4
2.3	<i>Abbreviations</i>	5
<b>3</b>	<b>Safety</b>	<b>5</b>
3.1	<i>Radiation Safety</i>	5
<b>4</b>	<b>Personnel qualifications</b>	<b>5</b>
<b>5</b>	<b>Equipment and materials</b>	<b>6</b>
5.1	<i>Equipment</i>	6
5.2	<i>Films</i>	6
5.3	<i>Image Quality Indicator (IQI)</i>	7
5.4	<i>Densitometer</i>	7
<b>6</b>	<b>Examination</b>	<b>8</b>
6.1	<i>Choice of examination energy / radioactive source</i>	8
6.2	<i>Surface preparations</i>	8
6.3	<i>Backscatter radiation check</i>	8
6.4	<i>System of identification</i>	9
6.5	<i>Monitoring density limitations of radiographs</i>	9
6.6	<i>Radiographic technique</i>	9
6.7	<i>Direction of radiation</i>	10
6.8	<i>Geometric un-sharpness</i>	10
6.9	<i>Location markers</i>	10
6.10	<i>IQI selection</i>	11
6.11	<i>IQI(s) placement</i>	11
6.12	<i>Number of IQIs</i>	12
6.13	<i>Shims under hole type IQIs</i>	12
6.14	<i>Number of exposures for circumferential welds</i>	12
<b>7</b>	<b>Evaluation of the radiograph</b>	<b>13</b>
7.1	<i>Quality of radiographs</i>	13
7.2	<i>Radiographic density</i>	13
7.3	<i>IQI sensitivity</i>	13
7.4	<i>Excessive backscatter</i>	13
7.5	<i>Acceptance criteria radiograph</i>	14
<b>8</b>	<b>Report</b>	<b>14</b>
8.1	<i>Radiograph review form.</i>	14
	<b>Attachment A Exposure arrangements</b>	<b>15</b>
	<b>Attachment B Number of exposures table (guideline)</b>	<b>17</b>
	<b>Attachment C Location markers</b>	<b>19</b>
	<b>Attachment D IQI wire / hole number, thickness and type</b>	<b>20</b>

	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

## 1 Scope

This procedure describes the method of examination of welds (up to 75 mm) and materials including castings in metallic materials according to the requirements as described in the:

- ASME BPVC Section V, article 2 edition 2021.

## 2 References and abbreviations


For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

### 2.1 Applus+ documents

- NL-10 Written practice for the Training, Qualification, Certification and Authorization of NDT Personnel.
- CP 31003 Verification procedure for film densitometers.
- CP 31014 Verification procedure for illuminators used for industrial radiographs.

### 2.2 Codes and standards

- ASME BPVC Section V ASME Boiler and Pressure Vessel Code, an International Code, Non-destructive Examination.
- ASTM E-747 Standard Guide for Design, Manufacturing and Material Grouping Classification of Wire IQI used for Radiology.
- ASTM E-999 Standard Guide for Controlling the Quality of Industrial Radiographic Film Processing.
- ASTM E-1025 Standard Practice for Design, Manufacture, and Material Grouping of Hole-Type IQI used for Radiology.
- ASTM E-1165 Standard Test Method for Measurement of Focal Spots of Industrial X-Ray Tubes by Pinhole Imaging.
- ISO 11699-1 Non-destructive testing - Industrial radiographic film - Part 1: Classification of film systems for industrial radiography
- ISO 19232-1 Non-destructive testing — Image quality of radiographs — Part 1: Determination of the image quality value using wire-type image quality indicators.
- ISO 19232-2 Non-destructive testing — Image quality of radiographs — Part 2: Determination of the image quality value using step/hole-type image quality indicators
- ISO 9712: 2012 Qualification and certification of NDT personnel.
- SNT-TC-1A : 2016 Personnel qualification and certification in non-destructive testing.
- CI 5A/5B Ionizing radiation course.

	
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

### 2.3 Abbreviations

b	Object to film distance.
D	Distance from source of radiation to weld or object being radiographed.
D <sub>e</sub>	Nominal external diameter of the pipe
d	Distance from source side of weld or object being radiographed to the film.
DWE	Double Wall Exposure.
DWV	Double Wall Viewing.
F	Source size: the maximum projected dimension of the radiating source (or effective focal spot) in the plane perpendicular to the distance D from the weld or object being radiographed.
f <sub>min</sub>	Minimum source to object distance.
HSE	Health Safety and Environment.
IQI	Image quality indicator.
kV	kilo Voltage.
mA	milli Amperage.
NDT	Non Destructive Testing.
RT	Radiographic Testing.
S	Radiation source.
SWE	Single Wall Exposure.
SWV	Single Wall Viewing.
t	Nominal Wall thickness.
U <sub>g</sub>	Geometric unsharpness.
w	Penetrated Thickness.

## 3 Safety

All applicable laws and regulations on both Applus+ HSE rules and Clients HSE rules shall be observed at all times.

In case of conflict between the different rules and regulations, the strictest will prevail.

### 3.1 Radiation Safety

Exposure of any part of the human body to X-ray or  $\gamma$ -ray can be highly injurious to health. Wherever X-ray or  $\gamma$ -ray equipment is in use, adequate precautions shall be taken to protect the radiographer and any other person in the vicinity.

Established safety precautions shall be strictly observed and everyone working with ionising radiation shall be certified with a radiation safety course.

For radiation monitoring only calibrated dose rate meters shall be used.

Maximum radiation at the border marked with radiation signs of the radiation working shall be in accordance with local regulations.

At least one of the crew operators shall have followed and passed a radiation safety course like CI 5A/5B, TMS or equivalent.


## 4 Personnel qualifications

NDE personnel shall be qualified and certified in accordance with the valid version of Applus+ Written Practice, which is in conformity with ISO 9712 and SNT-TC-1A.

The radiographic examination should be performed by personnel qualified with level RT 2 as minimum.

RT level 1 personnel and trainees shall only perform the examination under supervision of RT level 2 personnel as minimum.

All NDE personnel shall have passed a current eyesight examination within the past 12 months, according to the ISO 9712 section 7.4 or equivalent.

NARGAN COMPANY	
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
REVISION DATE: 16 Dec 2023	
SIGN: 	

## 5 Equipment and materials

### 5.1 Equipment

For X-ray:

Tube energy range up to 300 kV.

For examination of aluminium welds an X-ray tube with Beryllium window shall be used.

For  $\gamma$ -ray:

Iridium 192 (Ir192).

Selenium 75 (Se75).

Cobalt 60 (Co60).

### 5.2 Films

The films to be used shall be in accordance to the ISO 11699-1, class C5 (e.g. Agfa D7) or better.

The films must be free of defects that disturb the evaluation of the results of the radiographic examination.

The following disturbances are also unacceptable:

- Repairs carried out on films due to improper treatment or development.
- Scratches and contamination.
- Static discharge.
- Indications of defect screens or carrier errors.

#### 5.2.1 Developing of films

Developing of films should be done automatically or manual in accordance to SE-999 and chemicals of the manufacturers developing machine conditions.

Tenability of the radiographs shall be at least 10 years. This can be verified with a Thiosulphate test.

#### 5.2.2 Storage of films


All unexposed films shall be stored in a clean, dry place where the conditions will not detrimentally affect the emulsion. If any question arises about the condition of the unexposed film, sheets from the front and back of each package or a length of film equal to the circumference of each original roll shall be processed in the normal manner without exposure to light or radiation.

If the processed film shows fog, the entire box or roll from which the test film was removed shall be discarded, unless additional tests prove that the density of the remaining film is less than 0.3.

#### 5.2.3 Screens

Ready pack films without lead screen shall be used when applied energy is below 100 kV.

Ready pack films with lead screens 0.027 mm thickness on front and back side of the film shall be used when applied energy is over 100 kV.

NARGAN COMPANY	
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

### 5.3 Image Quality Indicator (IQI)

IQIs shall be either the wire type or hole type.

Wire-type IQIs shall be manufactured and identified in accordance with the requirements as per ASME BPVC V SE-747, except that the largest wire number or the identity number may be omitted.

Hole-type IQIs shall be manufactured and identified in accordance with the requirements as per ASME BPVC V SE-1025.

ASME BPVC V standard IQIs shall consist of those in Table T-233.2 for wire type and those in Table T-233.1 for hole type (refer to Attachment D: IQI-wire / hole number).

Alternate IQIs (e.g. ISO 19232-1 for wire type and ISO 19232-2 for hole type) are acceptable if the sensitivity is at least the thinnest required visible wire/hole as described in the ASME BPVC V article 2, as shown in Table 1: ASME and ISO material groups of this procedure.

In addition, any group IQI may be used for any material with a higher group number provided the applicable quality level is maintained.

ASME BPVC V material group		IQI material	Examined material	Equivalent IQI ISO 19232 -1 and -2
Light materials	01	Titanium	Titanium and alloys of which Titanium is the predominant alloying constituent	EN - TI
	02	Aluminium	Aluminium and alloys of which Aluminium is the predominant alloying constituent	EN - AL
Heavy materials	1	Carbon steel or Type 300 series Stainless steel	Carbon steel, low-alloy steels, stainless steels, and manganese-nickel-aluminium bronze (Superston).	EN - FE
	2	Aluminium Bronze (Alloy No. 623 of Specification B150M) or equivalent, or Nickel-Aluminium Bronze (Alloy No. 630 of Specification B150M) or equivalent	Aluminium Bronzes and all Nickel-Aluminium Bronzes	EN - Fe
	3	Nickel-chromium-iron alloy (UNS No. N06600) (Inconel)	Nickel-chromium-iron alloy and 18 % nickel-maraging steel	EN - Fe
	4	70 to 30 nickel-Copper alloy (Monel) (Class A or B of Specification B164) or equivalent, or 70 to 30 Copper-Nickel alloy (Alloy G of Specification B161) or equivalent	Nickel, copper, all nickel-copper series, or copper-nickel series of alloys, and all brasses (copper-zinc alloys). Group 4 IQI's may include the leaded brasses since leaded brass increases in attenuation with increase in lead content.	EN - CU
	5	Tin bronze (Alloy D of Specification B139/B139M).	Tin bronzes including gun-metal and valve bronze, or leaded-tin bronze of higher lead content than valve bronze. Group 5 IQI's may include bronze of higher lead content since leaded bronze increases in attenuation with increase in lead content. This would be equivalent to using a lower group IQI.	EN - CU

In addition, any group IQI may be used for any material with a higher group number provided the applicable quality level is maintained

INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN:	

Table 1: ASME and ISO material groups

### 5.4 Densitometer

A densitometer with valid verification according Applus+ verification procedure CP-31003 shall be used.

## 6 Examination

### 6.1 Choice of examination energy / radioactive source

The radiation energy employed for any radiographic technique shall achieve the density and IQI image requirements.

#### 6.1.1 Examination with X-ray

A guidance for the choice of maximum allowable energy:

- Steel, 100 kV + 8 kV/mm (w).
- Aluminium, 50 kV + 2 kV/mm (w).

#### 6.1.2 Examination with $\gamma$ -ray sources.

The recommended minimum penetrated thickness for which radioactive isotopes will be used as follows:

- For Ir192 applicable for  $20 \text{ mm} \leq w$ .
- For Se75 applicable for  $10 \text{ mm} \leq w \leq 40 \text{ mm}$ .
- Co60 for castings.

When it is not practical to perform radiography within the limitations outlined above, the procedure shall be proven satisfactory by actual demonstration of IQI image requirements on the required thickness of the material radiographed.

### 6.2 Surface preparations

#### 6.2.1 Welds

The weld ripples or weld surface irregularities on both the inside (where accessible) and outside shall be removed by any suitable process to such a degree that the image of surface irregularities cannot mask or be confused with the image of any discontinuity on the resulting radiograph.


#### 6.2.2 Materials including castings

Surfaces shall satisfy the requirements of the applicable materials specification or referencing Code Section, with additional conditioning, if necessary, by any suitable process to such a degree that the images of surface irregularities cannot mask or be confused with the image of any discontinuity on the resulting radiograph.

### 6.3 Backscatter radiation check

A lead symbol "B", with minimum dimensions of 11 mm in height and 1.5 mm in thickness, shall be attached to the back of each pre packed film during each exposure to determine if backscatter radiation is exposing the film.

The lead symbol "B" shall be placed in a location so that it would appear within an area on the radiograph that meets the density requirement.

	
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

## 6.4 System of identification

A system of identification shall be used to produce permanent identification on the radiograph traceable to:

- The contract.
- Component.
- Weld or weld seam or Part/object numbers.
- Date.

On clients request the following items can amended to the radiograph:

- The manufacturer's or stamp holder's symbol or name.
- NDT contractor's name or symbol.

This identification system does require that the information which is not appearing as radiographic image shall be recorded in another permanent way. In all cases, this information shall not obscure the area of interest.

### 6.4.1 Repair identification

Radiographs of repairs shall be identified by the letter R and may include -1, -2 etc. for the number of repairs or as otherwise agreed.

## 6.5 Monitoring density limitations of radiographs

A calibrated densitometer shall be used for measuring film density (see paragraph 5.4).

## 6.6 Radiographic technique

A single-wall exposure technique shall be used for radiography whenever practical.

When it is not practical to use a single-wall technique, a double-wall technique may be used. For exposure arrangements see Attachment A: Exposure arrangements.

### 6.6.1 Single-wall technique.

In the single-wall technique, the radiation passes through only one wall of the material (weld), which is viewed for acceptance on the radiograph.

### 6.6.2 Double-wall technique.

When it is not practical to use a single-wall technique, one of the following double-wall techniques shall be used.

(a) Single-wall viewing. For materials and for welds in components, a technique may be used in which the radiation passes through two walls and only the weld (material) on the film-side wall is viewed for acceptance on the radiograph, refer to Attachment B: guideline for number of exposures.

(b) Double-wall viewing. For materials and for welds in components  $\leq 89$  mm in nominal outside diameter, a technique may be used in which the radiation passes through two walls and the weld (material) in both walls is viewed for acceptance on the same radiograph.

(1) For welds, the radiation beam may be offset from the plane of the weld at an angle sufficient to separate the images of the source-side and film-side portions of the weld so that there is no overlap of the areas to be interpreted. When complete coverage is required, a minimum of two exposures taken  $90^\circ$  to each other shall be made for each joint.

(2) As an alternative, the weld may be radiographed with the radiation beam positioned so that the images of both walls are superimposed. When complete coverage is required, a minimum of three exposures taken at either  $60^\circ$  or  $120^\circ$  to each other shall be made for each joint.

(3) Additional exposures shall be made if the required radiographic coverage cannot be obtained using the minimum number of exposures indicated in (1) or (2) above.

INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
FREEZE/DATE: 16 Dec 2023	
SIGN:	

### 6.7 Direction of radiation

The direction of the central beam of radiation should be centred on the area of interest whenever practical.

### 6.8 Geometric unsharpness

Geometric unsharpness of the radiograph shall be determined with the following formula:

$$U_g = Fd/D$$

D and d shall be determined at the approximate center of the area of interest.

The geometric unsharpness of the radiograph shall not exceed:

- 0.51 mm for wall thickness under 50 mm.
- 0.76 mm for wall thickness from 50 through 75 mm.
- 1.02 mm for wall thickness from 75 through 100 mm.

### 6.9 Location markers

Location markers or measure tape markers (max. interval 50mm) shall be placed on the part, and shall appear as radiographic images on the film. Their locations or "0" point shall be permanently marked on the surface of the part being radiographed or on a map, in a manner that the area of interest on the radiograph is accurately traceable to its location and provide evidence on the radiograph that the required coverage of the region being examined has been obtained.

Location markers shall be placed as follows according to Attachment C: location markers.

#### 6.9.1 Single-wall viewing

(a) *Source side markers* Location markers shall be placed on the source side when radiographing the following:

1. Flat components or longitudinal joints in cylindrical or conical components.
2. Curved or spherical components whose concave side is toward the source and when the source to material distance is less than the inside radius of the component.
3. Curved or spherical components whose convex side is toward the source.

(b) *Film side markers* Location markers shall be placed on the film side when radiographing either curved or spherical components whose concave side is toward the source and when the source to material distance is equal to or greater than the inside radius.

#### 6.9.2 Double-wall viewing method

For double-wall viewing at least one location marker shall be placed on the source side surface adjacent to the weld (or on the material in the area of interest) for each radiograph.

#### 6.9.3 Mapping the placement of location markers

When inaccessibility or other limitations prevent the placement of markers as stipulated before dimensioned map of the actual marker placement shall accompany the radiographs and shall show that full coverage been obtained.

	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

### 6.10 IQI selection

IQI(s) shall be selected from either the same alloy material group or grade, or from a group with less radiation absorption than the material being radiographed. The designated hole or essential wire shall be as specified in the table below.

A smaller hole or a thinner wire than listed for each range may be used, provided equivalent penetrameter sensitivity and all other requirements for radiography are met.

The thickness on which the IQI is based is the nominal single-wall material thickness plus the weld reinforcement thickness estimated to be present on both sides of the weld (I.D. and O.D.). The values used for the estimated weld reinforcement thicknesses shall be representative of the weld conditions and shall not exceed the maximums permitted by the referencing Code Section. Physical measurement of the actual weld reinforcements is not required. Backing rings or strips shall not be considered as part of the thickness in IQI selection

Required sensitivity for hole-type IQI is the 2T-hole and for wire-type IQI is the essential wire number see table IQI selection.

Single Wall Material Thickness Range plus estimated weld reinforcement [mm]	Source Side			Film Side		
	Essential ISO wire	Essential ASTM wire	Plate No. 2T hole	Essential ISO wire	Essential ASTM wire	Plate No. 2T hole
Up to 6.4 incl.	13	5	12	14	4	10
Over 6.4 through 9.5	12	6	15	13	5	12
Over 9.5 through 12.7	11	7	17	12	6	15
Over 12.7 through 19.0	10	8	20	11	7	17
Over 19.0 through 25.4	9	9	25	10	8	20
Over 25.4 through 38.1	8	10	30	9	9	25
Over 38.1 through 50.8	7	11	35	8	10	30
Over 50.8 through 63.5	6	12	40	7	11	35
Over 63.5 through 101.6	5	13	50	6	12	40

Table 2: IQI selection

Note; if on request where the IQI(s) are placed on the film side, the technique shall be qualified by demonstrating the required sensitivity with a source side IQI on a test piece.

### 6.11 IQI(s) placement

The IQI(s) shall be placed on the source side of the part being examined, except for the condition described in 6.12.2.

When, due to part or weld configuration or size, it is not practical to place the IQI(s) on the part or weld, the IQI(s) may be placed on a separate block. Separate blocks shall be made of the same or radiographically similar materials (as defined in table 1) and may be used to facilitate IQI positioning. There is no restriction on the separate block thickness, provided the IQI/area-of-interest density tolerance requirements are met.

The IQI(s) identification and the letter "F" if used shall not in the area of interest, except when geometric configuration makes it impractical.

<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN:	

### 6.11.1 IQI(s) location

The hole type IQI(s) will be placed adjacent to or on the weld (see Figure 1). The wire type IQI(s) will be placed on the weld so that the length of the wires is across the length of the weld (see Figure 2) and not parallel to the weld (see Figure 3).



Figure 1: Hole type IQI



Figure 2: Wire type IQI



Figure 3: Not correct IQI placement

### 6.11.2 Film side IQI(s)

Where inaccessibility prevents hand placing the IQI(s) on the source side, it shall be placed on the film side in contact with the part being examined. A lead letter "F" shall be placed adjacent to or on the IQI(s).

### 6.12 Number of IQIs

For objects where one or more films are used for an exposure, at least one IQI image shall appear on each radiograph except for cylindrical welds where the source is placed on the axis of the object and one or more film holders are used for a single exposure of a complete circumference three IQIs shall be spaced approximately 120° apart. Where sections of longitudinal welds adjoining the circumferential weld are radiographed simultaneously, an additional IQI shall be placed on each longitudinal weld at the end of each section most remote from the junction with the circumferential weld being radiographed.

### 6.13 Shims under hole type IQIs

A shim of material radiographically similar to the weld metal shall be placed between the part and the hole type IQI, if needed, so that the radiographic density throughout the area of interest is no more than minus 15% (lighter than) the radiographic density through the IQI. The shim dimensions shall exceed the IQI dimensions such that the outline of at least three sides of the IQI image shall be visible on the radiograph.

### 6.14 Number of exposures for circumferential welds

An adequate number of exposures shall be made to demonstrate that the required coverage has been obtained.

Number of exposures (as shown in Attachment D) can be used as a guide line, for x-rays and gamma-rays.

<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN:	

## 7 Evaluation of the radiograph

### 7.1 Quality of radiographs

All radiographs shall be free from mechanical, chemical, or other blemishes to the extent that they cannot mask or be confused with the image of any discontinuity in the area of interest of the object being radiographed.

Such blemishes include, but are not limited to:

- Fogging.
- Processing defects such as streaks, watermarks, or chemical stains.
- Scratches, finger marks, crimps, dirtiness, static marks, smudges, or tears.
- False indications due to defective screens.

### 7.2 Radiographic density

#### 7.2.1 Density limitations

The transmitted film density through the radiographic image of the body of the designated IQI and the area of interest shall be 1.8 minimum for single film viewing for radiographs made with an X-ray source and 2.0 minimum for radiographs made with a gamma ray source.

The maximum density shall be 4.0 for single film viewing, the maximum density of the film assessed shall never exceed the light intensity incident of the viewer.

A tolerance of 0.05 in density is allowed for variations between densitometer readings.

#### 7.2.2 Density variation

If the density of the radiograph anywhere through the area of interest varies more than minus 15% or plus 30% from the density through the body of the hole type IQI or adjacent to the designated wire of the wire IQI, within the minimum/maximum allowable density ranges specified above, then an additional IQI shall be used for each exceptional area or areas and the radiograph retaken. When calculating the allowable variation in density, the calculation may be rounded to the nearest 0.1 within the range specified above.

When shims are used the plus 30% density restriction may be exceeded and the minimum mentioned above does not apply, provided the required IQI sensitivity is met.

### 7.3 IQI sensitivity

Radiography shall be performed with a technique of sufficient sensitivity to display the designated hole type IQI image and the essential hole or essential wire of the wire type IQI. The radiographs shall also display the IQI identifying numbers and letters. For wire-type IQIs, the essential wire shall be visible within the area of interest representing the thickness used for determining the essential wire, inclusive of the allowable density variations.

### 7.4 Excessive backscatter

If a light image of the "B", specified in 6.3, appears on a darker background of the radiograph, protection from backscatter is insufficient and the radiograph shall be considered unacceptable. A dark image of "B" on a lighter background will be acceptable if the image cannot be confused with a defect.

	NARGAN COMPANY
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI	DATE: 16 Dec 2023
SIGN:	

### 7.5 Acceptance criteria radiograph

Density X-ray 1.8 – 4.0 according paragraph to 7.2.

Density Y-ray 2.0 – 4.0 according paragraph to 7.2.

Required IQI visible in area of interest according paragraph to 6.11.

No excessive backscatter or light B according paragraph to 6.4.

Film identification, weld number, date, manufacture logo and object according paragraph to 6.5.

Text and measurement markers not in area of interest.

Number of films considering effective film length.

## 8 Report



For a proper interpretation of the radiographs, the report accompanying each group of radiographs shall contain, as a minimum, the following information:

- Procedure and revision number used.
- Identification to the contract, component and weld.
- Identification of exposure arrangement.
- Map of location marker placement, when applicable.
- Number of exposures.
- Isotope or applied X-ray kV.
- Effective focal spot sizes (F).
- Material type and thickness range, weld thickness and reinforcement.
- Source-to-object distance (D).
- Distance from source side of object to film (d).
- Film brand and designation.
- Number of films per cassette.
- Single- or double-wall exposure/viewing.
- Date of examination.
- Name and level personnel.

### 8.1 Radiograph review form.

The Manufacturer shall be responsible for the preparation of a radiograph review form. As a minimum, the following information shall be provided:

- A listing of each radiograph location.
- Evaluation and disposition of the weld(s) examined.
- Identification of the manufacturer's representative who performed the final acceptance of the radiographs (if applicable).
- Date of manufacturer's evaluation (if applicable).

	NARGAN COMPANY
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

### Attachment A Exposure arrangements

Pipe O.D.	Exposure technique	Radiograph Viewing	Source-Weld-Film Arrangement		IQI		Location marker placement
			End view	Side view	selection	placement	
Any	Single wall 6.6.1	Single wall	<p>Exposure arrangement - A</p>		6.10	6.11 Source or film side	Attachment C
Any	Single wall 6.6.1	Single wall	<p>Exposure arrangement - B</p>		6.10	6.11 Source or film side	Attachment C
Any	Single wall 6.6.1	Single wall	<p>Exposure arrangement - C</p>		6.10	6.11 Source side	Attachment C
Any	Double wall 6.6.2	Single wall	<p>Exposure arrangement - D</p>		6.10	6.11 Source or film side	Attachment C
Any	Double wall 6.6.2	Single wall	<p>Exposure arrangement - E</p>		6.10	6.11 Source or film side	Attachment C

NARGAN COMPANY	
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
REVISION DATE: 16 Dec 2023	
SIGN:	





<p>≤ 89 mm</p>	<p>Double wall 6.6.2</p>	<p>Double wall</p>	 <p>Exposure arrangement - F</p>	<p>6.10</p>	<p>6.11 Source side</p>	<p>Attachment C</p>
<p>≤ 89 mm</p>	<p>Double wall 6.6.2</p>	<p>Double wall</p>	 <p>Exposure arrangement - G</p>	<p>6.10</p>	<p>6.11 Source side</p>	<p>Attachment C</p>

Table 3: Radiographic techniques

	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

## Attachment B Number of exposures table (guideline)

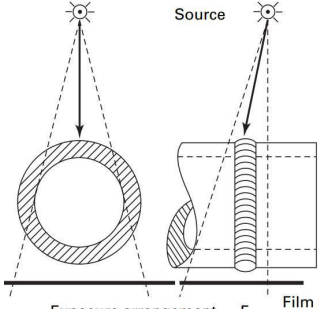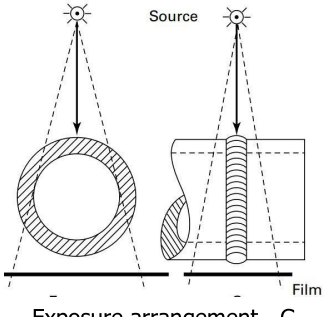The tables 4 and 5 are a guidelines for the number of exposures, the final number of exposures shall be chosen based on the effective film length and overlap.

If for diameters up to 3" the DWDI technique will be used, the number of exposures will be demonstrated so that the weld coverage is within the requirements as described in this procedure.

X-ray		Schedule																
Diameter		5s	10s	10	20	30	STD 40s	40	60	XS 80s	80	100	120	140	160	XXS	inch	
inch	mm																	
1/2	21,3	2/3	2/3	---	---	---	2/3	2/3	---	2/3	2/3	---	---	---	2/3	2/3	1/2	
3/4	26,7	2/3	2/3	---	---	---	2/3	2/3	---	2/3	2/3	---	---	---	2/3	3	3/4	
1	33,4	2/3	2/3	---	---	---	2/3	2/3	---	2/3	2/3	---	---	---	2/3	3	1	
1 1/4	42,2	2/3	2/3	---	---	---	2/3	2/3	---	2/3	2/3	---	---	---	2/3	3	1 1/4	
1 1/2	48,3	2/3	2/3	---	---	---	2/3	2/3	---	2/3	2/3	---	---	---	2/3	3	1 1/2	
2	60,3	2/3	2/3	---	---	---	2/3	2/3	---	2/3	2/3	---	---	---	3	3	2	
2 1/2	73,0	2/3	2/3	---	---	---	2/3	2/3	---	2/3	2/3	---	---	---	3	3	2 1/2	
3	88,9	2/3	2/3	---	---	---	2/3	2/3	---	2/3	2/3	---	---	---	3	3	3	
3 1/2	101,6	5	5	---	---	---	5	5	---	5	5	---	---	---	---	---	3 1/2	
4	114,3	5	5	---	---	---	5	5	---	5	5	---	5	---	5	6	4	
5	141,3	5	5	---	---	---	5	5	---	5	5	---	5	---	5	5	5	
6	168,3	5	5	---	---	---	5	5	---	5	5	---	5	---	5	5	6	
8	219,1	4	4	---	4	4	5	5	5	5	5	5	5	5	5	5	8	
10	273,1	4	4	---	4	4	4	4	4	4	4	4	5	5	5	5	10	
12	323,9	4	4	---	4	4	4	4	4	4	4	4	4	5	5	4	12	
14	355,6	4	4	4	4	4	4	4	4	4	4	4	4	4	5	---	14	
16	406,4	4	4	4	4	4	4	4	4	4	4	4	4	4	4	---	16	
18	457,2	4	4	4	4	4	4	4	4	4	4	4	4	4	4	---	18	
20	508,0	4	4	4	4	4	4	4	4	4	4	4	4	4	4	---	20	
22	558,8	---	---	4	4	4	4	---	4	4	4	4	4	4	4	---	22	
24	609,6	4	4	4	4	4	4	4	4	4	4	4	4	4	4	---	24	
26	660,4	---	---	4	4	---	4	---	---	4	---	---	---	---	---	---	26	
28	711,2	---	---	4	4	4	4	---	---	4	---	---	---	---	---	---	28	
30	762,0	---	---	4	4	4	4	---	---	4	---	---	---	---	---	---	30	
32	812,8	---	---	4	4	4	4	4	---	4	---	---	---	---	---	---	32	
34	863,8	---	---	4	4	4	4	4	---	4	---	---	---	---	---	---	34	
36	914,4	---	---	4	4	4	4	4	---	4	---	---	---	---	---	---	36	
42	1067,0	Wallthickness 8,74 up to including 25,4 mm					4				4							42
48	1219,0	Wallthickness 8,74 up to including 25,4 mm					4				4							48

Table 4: X-Ray exposure guideline.

Code 2/3 means: 2 exposures, the elliptical technique "F" at 90° to each other or 3 exposures, superimposed technique "G" at 60° or 120° to each other.

<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN:	

Doc Ref : RT 21002  
 Revision : 29  
 Date : 16-12-2021  
 Title : Radiographic examination  
 Type : Standard procedure



Se75 / Ir192		Schedule																
Diameter		5s	10s	10	20	30	STD 40s	40	60	XS 80s	80	100	120	140	160	XXS	inch	
inch	mm																	
1/2	21,3	2/3	2/3	---	---	---	2/3	2/3	---	2/3	2/3	---	---	---	2/3	2/3	1/2	
3/4	26,7	2/3	2/3	---	---	---	2/3	2/3	---	2/3	2/3	---	---	---	2/3	3	3/4	
1	33,4	2/3	2/3	---	---	---	2/3	2/3	---	2/3	2/3	---	---	---	2/3	3	1	
1 1/4	42,2	2/3	2/3	---	---	---	2/3	2/3	---	2/3	2/3	---	---	---	2/3	3	1 1/4	
1 1/2	48,3	2/3	2/3	---	---	---	2/3	2/3	---	2/3	2/3	---	---	---	2/3	3	1 1/2	
2	60,3	2/3	2/3	---	---	---	2/3	2/3	---	2/3	2/3	---	---	---	3	3	2	
2 1/2	73,0	2/3	2/3	---	---	---	2/3	2/3	---	2/3	2/3	---	---	---	3	3	2 1/2	
3	88,9	2/3	2/3	---	---	---	2/3	2/3	---	2/3	2/3	---	---	---	3	3	3	
3 1/2	101,6	3	3	---	---	---	3	3	---	4	4	---	---	---	---	---	3 1/2	
4	114,3	3	3	---	---	---	3	3	---	4	4	---	4	---	4	4	4	
5	141,3	3	3	---	---	---	3	3	---	3	3	---	4	---	4	4	5	
6	168,3	3	3	---	---	---	3	3	---	3	3	---	4	---	4	4	6	
8	219,1	3	3	---	3	3	3	3	3	3	3	3	4	4	4	4	8	
10	273,1	3	3	---	3	3	3	3	3	3	3	3	4	4	4	4	10	
12	323,9	3	3	---	3	3	3	3	3	3	3	3	4	4	4	4	12	
14	355,6	3	3	3	3	3	3	3	3	3	3	3	4	4	4	---	14	
16	406,4	3	3	3	3	3	3	3	3	3	3	3	4	4	4	---	16	
18	457,2	3	3	3	3	3	3	3	3	3	3	3	4	4	4	---	18	
20	508,0	3	3	3	3	3	3	3	3	3	3	3	4	4	4	---	20	
22	558,8	3	3	3	3	3	3	---	3	3	3	3	4	4	4	---	22	
24	609,6	3	3	3	3	3	3	3	3	3	3	3	4	4	4	---	24	
26	660,4	---	---	3	3	---	3	---	---	3	---	---	---	---	---	---	26	
28	711,2	---	---	3	3	3	3	---	---	3	---	---	---	---	---	---	28	
30	762,0	3	3	3	3	3	3	---	---	3	---	---	---	---	---	---	30	
32	812,8	---	---	3	3	3	3	3	---	3	---	---	---	---	---	---	32	
34	863,8	---	---	3	3	3	3	3	---	3	---	---	---	---	---	---	34	
36	914,4	---	---	3	3	3	3	3	---	3	---	---	---	---	---	---	36	
42	1067,0	Wallthickness 8,74 up to including 25,4 mm					3				3							42
48	1219,0	Wallthickness 8,74 up to including 25,4 mm					3				3							48

Table 5: Y-Ray exposure guideline

Code 2/3 means: 2 exposures, the elliptical technique "F" at 90° to each other or 3 exposures, superimposed technique "G" at 60° or 120° to each other.

INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN:	

## Attachment C Location markers

ASME BPVC V Figure T-275, location marker sketches.

<p>Figure 4: Flat component or longitudinal seam</p>	<p>Figure 5: Curved components with radiation source to film distance less than radius of component</p>	<p>Figure 6: Curved components with convex surface towards radiation source</p>
<p>Figure 7: Curved components with radiation source to film distance greater than radius of curvature</p>	<p>Figure 8: Source side marker alternate flat component or longitudinal seam</p> $X = (t/D)(M_f/2)$ <p>X = additional required coverage beyond film side location marker.        t = component thickness        M<sub>f</sub> = film side location marker interval        D = source to component distance</p>	<p>Figure 9: Curved components with radiation source at center curvature</p>
<p>LEGEND: Radiation source — ☆        Location marker — •        Component center — +</p>		

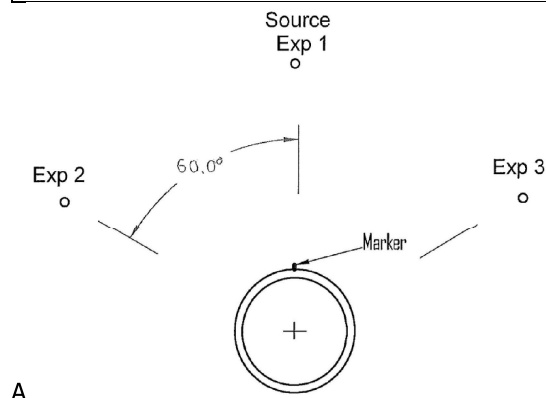


Figure 10: Location marker(s) on a small bore pipe

<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
<small>BY: M. REZAEI DATE: 16 Dec 2023</small>	
<small>SIGN: </small>	

Attachment D **IQI wire / hole number, thickness and type**

IQI according ASME BPVC V SE-747					IQI according EN-ISO 19232-1				
Ø wire		IQI set			Ø wire	IQI set			
[In.]	[mm]	A	B	C	[mm]	13-19	10-16	6-12	1-6
					0.050	19			
					0.063	18			
0.0032	0.08	1			0.080	17			
0.004	0.1	2			0.100	16	16		
0.005	0.13	3			0.125	15	15		
0.0063	0.16	4			0.16	14	14		
0.008	0.2	5			0.20	13	13		
0.010	0.25	6	6		0.25		12	12	
0.013	0.33		7		0.32		11	11	
0.016	0.4		8		0.40		10	10	
0.020	0.51		9		0.50			9	
0.025	0.64		10		0.63			8	
0.032	0.81		11	11	0.80			7	7
0.040	1.02			12	1.00			6	6
0.050	1.27			13	1.25				5
0.063	1.6			14	1.60				4
0.080	2.03			15	2.00				3
0.100	2.5			16	2.50				2
					3.20				1

Table 6: ASME BPVC V IQI set versus ISO 19232-1 IQI set.

IQI Designation	IQI thickness		1T hole diameter		2T hole diameter		4T hole diameter	
	[In.]	[mm]	[In.]	[mm]	[In.]	[mm]	[In.]	[mm]
5	0.005	0.13	0.010	0.25	0.020	0.51	0.040	1.02
7	0.0075	0.19	0.010	0.25	0.020	0.51	0.040	1.02
10	0.010	0.25	0.010	0.25	0.020	0.51	0.040	1.02
12	0.0125	0.32	0.0125	0.32	0.025	0.64	0.050	1.27
15	0.015	0.38	0.015	0.38	0.030	0.76	0.060	1.52
17	0.0175	0.44	0.0175	0.44	0.035	0.89	0.070	1.78
20	0.020	0.51	0.020	0.51	0.040	1.02	0.080	2.03
25	0.025	0.64	0.025	0.64	0.050	1.27	0.100	2.54
30	0.030	0.76	0.030	0.76	0.060	1.52	0.120	3.05
35	0.035	0.89	0.035	0.89	0.070	1.78	0.140	3.56
40	0.040	1.02	0.040	1.02	0.080	2.03	0.160	4.06
45	0.045	1.14	0.045	1.14	0.090	2.29	0.180	4.57
50	0.050	1.27	0.050	1.27	0.100	2.54	0.200	5.08




Table 7: Hole-type IQI designation, thickness and hole diameters

Doc Ref : RT 21005  
 Revision : 28  
 Date : 16-12-2021  
 Title : Radiographic assessment procedure  
 Type : Standard procedure







## RADIOGRAPHIC ASSESSMENT PROCEDURE

Assessment of radiographic examination of welded joints in accordance with the requirements of one of the following standards:

- ASME BPVC Section I, edition 2021, paragraph PW 51**
- ASME BPVC Section VIII Division 1, edition 2021, paragraph UW 51**
- ASME BPVC Section VIII Division 1, edition 2021, paragraph UW 52**
- ASME BPVC Section VIII Division 2, edition 2021, paragraph 7.5.3.2**
- ASME BPVC Section IX, edition 2021, paragraph QW 191.1.2**
- ASME code for Power Piping, B31.1: 2020, table 136.4.5**
- ASME code for Process Piping, B31.3: 2020, table 341.3.2**

Development – Revisions					
Revision No.	Prepared By	Date	Approved By	Date	Amendment Details
28	T. Cornelissen	16-12-2021	T. Speelmeijer	16-12-2021	
27		02-04-2021			
0		01-08-1991			


 Digitally signed by Theo Cornelissen  
 Date: 2021.12.17 08:56:43 +01'00'  
 Theo Speelmeijer  
 MT3 PT3 RT3 UT3  


 NARGAN COMPANY	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

Date: 16-12-2021      Date: 16-12-2021      Date:

Address  
 Delftweg 144, 3046 NC Rotterdam  
 P.O. Box 10065, 3004 AB Rotterdam  
 The Netherlands  
[www.ApplusRTD.com](http://www.ApplusRTD.com)

This publication is the intellectual property of Applus+ and may not be used in whole or in part for any purpose other than the business of Applus+ and may not be used for the business of the recipient and may not be passed to any other person without the permission of Applus+.

Doc Ref : RT 21005  
 Revision : 28  
 Date : 16-12-2021  
 Title : Radiographic assessment procedure  
 Type : Standard procedure





## Revision History

Revision Number	Date	Section	Brief Description of change	Author of Change
0	01-08-1991		Issued as new document	
18	14-12-2010	1, 2.1	updated to the ASME BPVC VIII 2010	R. Coenen
19	14-12-2011	1, 2.1	updated to the ASME BPVC VIII 2010 addenda 2011	R. Coenen
20	01-06-2012	2.1		R. Coenen
21	10-01-2014	2.1, 2.2, 2.3		R. Coenen
22	21-10-2015		updated to the ASME BPVC VIII 2015 edition	P. Briggeman
23	13-12-2017		updated to the ASME BPVC VIII 2017 edition	P. Briggeman
24	07-01-2020		Complete revised and updated to the ASME BPVC VIII 2019 edition	T. Cornelissen
25	01-12-2020		Amended several ASME acceptance standards	T. Cornelissen
26	05-03-2021	10 update ASME B31.1 Table removed from 5.1.2, 6.1.1, 8.3	Updated ASME B31.1 to 2020 version and typo's corrected, indicated in margins	T. Cornelissen
27	02-04-2021	5.1.1, 6.1.6, 10.2	References corrected	T. Cornelissen
28	16-12-2021	1, 10.2	Updated to the latest ASME editions	T. Cornelissen

<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN:	

## Contents

<b>1</b>	<b>Scope</b>	<b>4</b>
<b>2</b>	<b>References and abbreviations</b>	<b>4</b>
2.1	<i>Applus+ documents</i>	4
2.2	<i>Codes and standards</i>	4
2.3	<i>Abbreviations</i>	4
2.4	<i>Definitions</i>	5
<b>3</b>	<b>Personnel qualifications</b>	<b>5</b>
<b>4</b>	<b>General requirements</b>	<b>5</b>
4.1	<i>Facilities for viewing of radiographs</i>	5
4.2	<i>Radiographic quality</i>	5
4.3	<i>Report</i>	6
<b>5</b>	<b>ASME BPVC Section I, paragraph PW 51</b>	<b>7</b>
5.1	<i>Evaluation</i>	7
5.2	<i>Rounded indication charts</i>	8
5.3	<i>Acceptance criteria</i>	10
<b>6</b>	<b>ASME BPVC Section VIII Division 1, paragraph UW 51</b>	<b>11</b>
6.1	<i>Evaluation</i>	11
6.2	<i>Acceptance criteria</i>	14
<b>7</b>	<b>ASME BPVC Section VIII Division 1, paragraph UW 52</b>	<b>15</b>
7.1	<i>Acceptance criteria</i>	15
<b>8</b>	<b>ASME BPVC Section VIII Division 2, paragraph 7.5.3.2</b>	<b>16</b>
8.1	<i>Evaluation</i>	16
8.2	<i>Acceptance criteria</i>	16
8.3	<i>Rounded indication charts</i>	16
<b>9</b>	<b>ASME BPVC Section IX, paragraph QW 191.1.2</b>	<b>20</b>
9.1	<i>Acceptance Criteria</i>	20
9.2	<i>Rounded indication chart</i>	20
<b>10</b>	<b>ASME B31.1, paragraph 136.4.5</b>	<b>21</b>
10.1	<i>Acceptance criteria linear indications</i>	21
10.2	<i>Acceptance criteria for rounded indications</i>	21
<b>11</b>	<b>ASME B31.3, table 341.3.2</b>	<b>22</b>
11.1	<i>Acceptance criteria for rounded indications</i>	22
11.2	<i>Table 341.3.2 Acceptance criteria for welds</i>	23

	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN:	

## 1 Scope

This procedure defines the radiographic assessment of radiographs which has been performed in accordance with the requirements of the ASME BPVC Section V, article 2.

Assessment of radiographic examination of welded joints will be in accordance with the requirements of one of the following standards and shall be specified by the client:

- ASME BPVC Section I, edition 2021, paragraph PW 51.
- ASME BPVC Section VIII Division 1, edition 2021, paragraph UW 51.
- ASME BPVC Section VIII Division 1, edition 2021, paragraph UW 52 (spot examination).
- ASME BPVC Section VIII Division 2, edition 2021, paragraph 7.5.3.2.
- ASME BPVC Section IX, edition 2021, paragraph QW 191.1.2.
- ASME code for Power Piping, B31.1: 2020, table 136.4.5.
- ASME code for Process Piping, B31.3: 2020, table 341.3.2.

## 2 References and abbreviations

For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

### 2.1 *Applus+ documents*


- NL-10 Written practice for the Training, Qualification, Certification and Authorization of NDT Personnel.
- CP 31003 Procedure for calibration of film densitometers.
- CP 31014 Verification procedure for illuminators used for industrial radiographs.

### 2.2 *Codes and standards*

- ASME BPVC I ASME Boiler and Pressure Vessel Code, an International Code, Rules for construction of power boilers.
- ASME BPVC V ASME Boiler and Pressure Vessel Code, an International Code, Non-destructive Examination.
- ASME BPVC VIII.1 ASME Boiler and Pressure Vessel Code, Division 1.
- ASME BPVC VIII.2 ASME Boiler and Pressure Vessel Code, Division 2.
- ASME BPVC IX ASME Boiler and Pressure Vessel Code, an International Code, Qualification Standard for Welding, Brazing, and Fusing Procedures; Welders; Brazers; and Welding, Brazing, and Fusing Operators.
- ASME B31.1 Power piping, ASME code for pressure piping, B31.
- ASME B31.3 Process piping, ASME code for pressure piping, B31.
- ISO 9712: 2012 Qualification and certification of NDT personnel.
- SNT-TC-1A: 2016 Personnel qualification and certification in NDT.

### 2.3 *Abbreviations*

ASME BPVC	ASME Boiler Pressure Vessel code
IQI	Image Quality Indicator
NDT	Non Destructive Testing
RT	Radiographic Testing
<i>t</i>	Nominal thickness of the parent material only where manufacturing tolerances do not have to be taken into account.

	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

## 2.4 Definitions

### Rounded indications

Indications with a maximum length of three times the width or less on the radiograph are defined as rounded indications. These indications may be circular, elliptical, conical or irregular in shape and may have tails. When evaluating the size of an indication, the tail shall be included. The indication may be from any imperfection in the weld, such as porosity, slag or tungsten.

### Aligned indications

A sequence of four or more rounded indications shall be considered to be aligned when they touch a line parallel to the length of the weld drawn through the centre of the two outer rounded indications.

### Elongated indications

Indications, not being a crack, lack of fusion or incomplete penetration, with a length greater than 3 times the width on the radiograph are defined as elongated indications.

### Thickness (t)

$t$  is the thickness of the weld, excluding any allowable reinforcement. For a butt weld joining two members having different thicknesses at the weld,  $t$  is the thinner of these two thicknesses. If a full penetration weld includes a fillet weld, the thickness of the fillet weld throat shall be included in  $t$ .

## 3 Personnel qualifications

NDT-personnel shall be qualified and certified in accordance with the valid version of Applus+ Written Practice NL-10, which is in conformity with the SNT-TC-1A and ISO 9712.

The assessment of the radiographs shall be performed only by certified personnel RT level 2 including Film Interpretation level 2 as minimum.

Shall have passed an eyesight examination within the past 12 months, according the ISO 9712 section 7.4 or equivalent.

## 4 General requirements

### 4.1 Facilities for viewing of radiographs

The proper assessment of image quality and accurate reporting on the diagnostic information of the radiographs shall be achieved by:

- The densitometer shall be verified according Applus+ procedure CP 31003 and shall have a valid certificate.
- The maximum density of the film assessed shall never exceed the light intensity incident of the film viewer.
- The film viewer and lamps shall be verified according Applus+ procedure CP 31014 and shall have a valid certificate.
- No light sources with a strength > 50 lux shall be visible when assessing the radiograph, to avoid dazzling.
- Means for magnifying details in the displayed radiographic image should be available. The magnifying glass shall be max 7x.
- The ambient light intensity measured on the film viewer (with the film viewer off) shall be  $\leq 20$  lux.

NARGAN COMPANY	
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

### 4.2 Radiographic quality

If the minimum requirement as described in the ASME BPVC V art.2 summerized in section 4.2.1 and 4.2.2 of this procedure are not met, the radiograph shall be rejected due to quality issues. If agreed between contracted parties the radiograph can maybe accepted.

#### 4.2.1 Radiographic density limitations

The transmitted film density through the radiographic image of the body of the appropriate IQI and the area of interest shall be 1.8 minimum for single film viewing for radiographs made with an X-ray source and 2.0 minimum for radiographs made with a gamma-ray source.

The maximum density shall be 4.0 for either single or composite viewing, the maximum density of the film assessed shall never exceed the light intensity incident of the viewer.

A tolerance of  $\pm 0.05$  in density is allowed for variations between densitometer readings.

#### 4.2.1 Weld reinforcement

If there is a question regarding the surface condition of the weld and the weld reinforcement when interpreting a radiographic film, the film shall be compared to the actual weld surface for determination of acceptability.

The values used for the estimated weld reinforcement thicknesses shall be representative of the weld conditions and shall not exceed the maximums permitted by the referencing Code Section. Physical measurement of the actual weld reinforcements is not required.

#### 4.2.2 IQI sensitivity

The minimum sensitivity requirements of the radiographs shall be as mentioned in Table 1 below.

The thickness on which the IQI is based is the nominal single-wall material thickness plus the weld reinforcement thickness estimated to be present on both sides of the weld (I.D. and O.D.).

Backing rings or strips shall not be considered as part of the thickness in IQI selection.



Single Wall Material Thickness Range plus estimated weld reinforcement [mm]	Source Side			Film Side		
	Essential ISO wire	Essential ASTM wire	Plate No. 2T hole	Essential ISO wire	Essential ASTM wire	Plate No. 2T hole
Up to 6.4 incl.	13	5	12	14	4	10
Over 6.4 through 9.5	12	6	15	13	5	12
Over 9.5 through 12.7	11	7	17	12	6	15
Over 12.7 through 19.0	10	8	20	11	7	17
Over 19.0 through 25.4	9	9	25	10	8	20
Over 25.4 through 38.1	8	10	30	9	9	25
Over 38.1 through 50.8	7	11	35	8	10	30
Over 50.8 through 63.5	6	12	40	7	11	35
Over 63.5 through 101.6	5	13	50	6	12	40

Table 1: IQI sensitivity requirements

#### 4.3 Report

The report shall be finalized with the results of the assessment, the following information shall be add to the report made for the examination as minimum by the radiograph interpreter:

- Procedure and revision number used.
- Relevant indications.
- Results of the assessment.
- Date of interpretation.
- Name and level personnel

	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

## 5 ASME BPVC Section I, paragraph PW 51

### 5.1 Evaluation

#### 5.1.1 Relevant indications

Only those rounded indications which exceed the following dimensions shall be considered relevant.

1/10t	for $t < 3.0$ mm.
0.4 mm	for $3 \text{ mm} \leq t \leq 6$ mm.
0.8 mm	for $6 \text{ mm} < t \leq 50$ mm.
1.6 mm	for $t > 50$ mm.


#### 5.1.2 Maximum size of rounded indications

The maximum permissible size of any indication shall be 1/4t, or 4 mm, whichever is smaller; except that an isolated indication separated from an adjacent indication by 25 mm or more may be 1/3t, or 6 mm, whichever is less. For t greater than 50 mm, the maximum permissible size of an isolated indication shall be increased to 10 mm.

#### 5.1.3 Aligned rounded indications


Aligned rounded indications are acceptable when the summation of the diameters of the indications is less than t in a length of 12t, refer to: rounded indication charts A-250-3.4-1.

The length of groups of aligned rounded indications and the spacing between the groups shall meet the requirements of: rounded indication charts A-250-3.4-2.

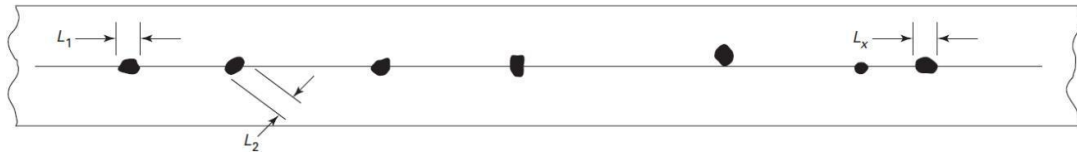

General note: Sum of  $L_2$  to  $L_x$  shall be less than  $t$  in a length of  $12t$ .

**Figure A-250 3.4-1.** Aligned rounded indications

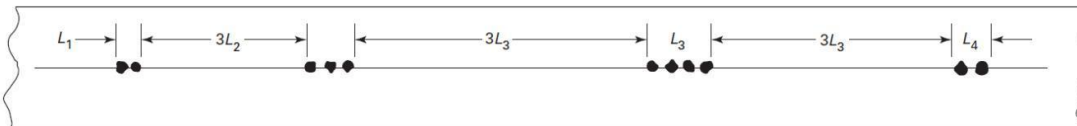

#### Maximum Group Length

L	=	6 mm for $t$ less than 19 mm
L	=	1/3t for $t$ 19 mm to 57 mm
L	=	19 mm for $t$ greater than 57 mm

#### Minimum Group Spacing

3L where L is the length of the longest adjacent group being evaluated

GENERAL NOTE: Sum of the group lengths shall be less than t in a length of  $12t$

**Figure A-250 3.4-2.** Groups of aligned rounded indications

#### 5.1.4 Spacing

The distance between adjacent rounded indications is not a factor in determining acceptance or rejection, except as required for isolated indications or groups of aligned indications.

NARGAN COMPANY	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN:	

### 5.1.5 Weld thickness $t$ less than 3.0 mm

For  $t$  less than 3.0 mm the maximum number of rounded indications shall not exceed 12 in any 150 mm weld length. A proportionally fewer number of indications shall be permitted in welds less than 150 mm in length.

### 5.1.6 Clustered indications


The illustrations for clustered indications show up to four times as many indications in a local area, as that shown in the illustrations for random indications. The length of an acceptable cluster shall not exceed the lesser of 25 mm or  $2t$ . Where more than one cluster present, the sum of the lengths of the clusters shall not exceed 25 mm in any 150 mm weld length.

## 5.2 Rounded indication charts


The rounded indications are characterized as imperfections shall not exceed that shown in the charts A-250.3.6-1 through A-250.3.6-5. These charts represent the maximum acceptable concentration limits for rounded indications in any 150 mm weld length.

Maximum size of individual rounded indications in the Figures A-250.3.6-1 up to A-250.3.6-5 shall be as per section 5.1.2.

The distributions shown are not necessarily the patterns that may appear on the radiograph, but are typical of the concentration and size of indications permitted.




(a) Random Rounded Indications  
Typical concentration and size permitted in any 150 mm length of weld.

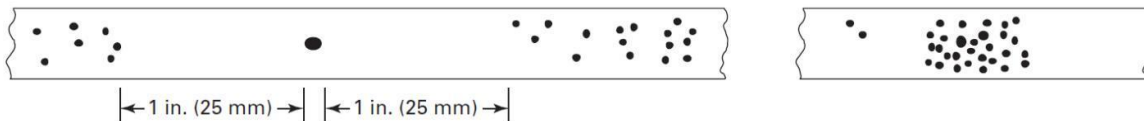


(b) Isolated Indication (c) Cluster

**Figure A-250 3.6-1.** Charts for  $t$  3 mm to 6 mm, inclusive




(a) Random Rounded Indications  
Typical concentration and size permitted in any 150 mm length of weld.

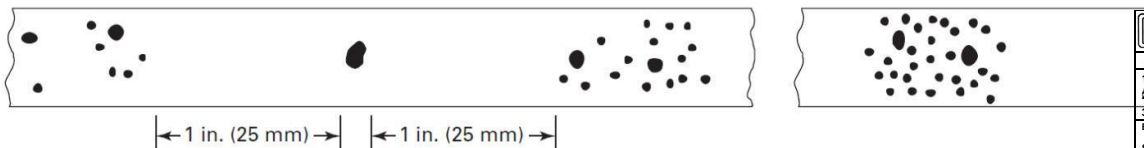


(b) Isolated Indication (c) Cluster

**Figure A-250 3.6-2.** Charts for  $t$  6 mm to 10 mm, inclusive

NARGAN COMPANY	
INSPECTION	
1. APPROVED	<input type="checkbox"/>
2. APPROVED AS NOTED	<input checked="" type="checkbox"/>
3. NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN:	

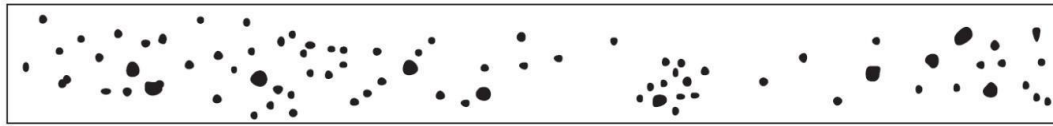


(a) Random Rounded Indications  
 Typical concentration and size permitted in any 150 mm length of weld.

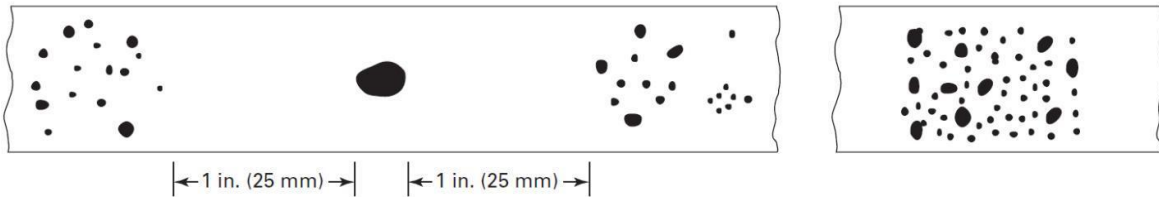


(b) Isolated Indication (c) Cluster

**Figure A-250.3.6-3.** Charts for  $t$  over 10 mm to 19 mm, inclusive

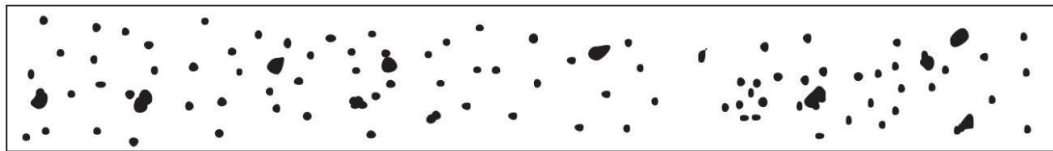


(a) Random Rounded Indications  
 Typical concentration and size permitted in any 150 mm length of weld.

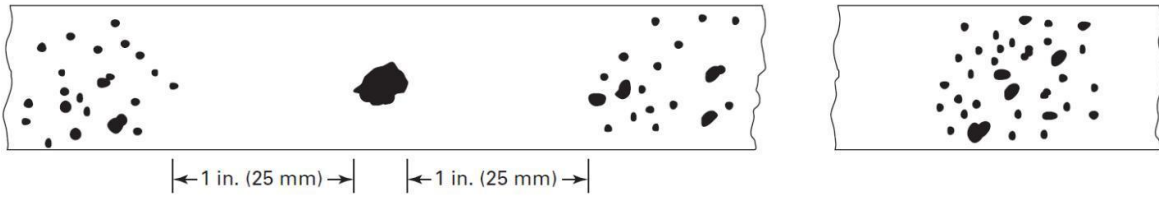


(b) Isolated Indication (c) Cluster

**Figure 250.3.6-4.** Charts for  $t$  over 19 mm to 50 mm, inclusive

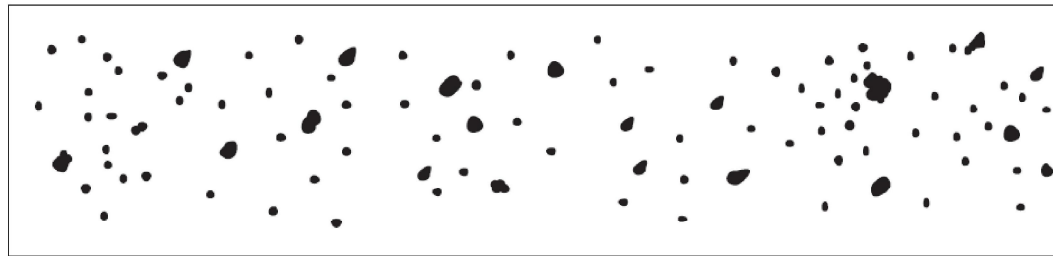

(a) Random Rounded Indications  
 Typical concentration and size permitted in any 150 mm length of weld.

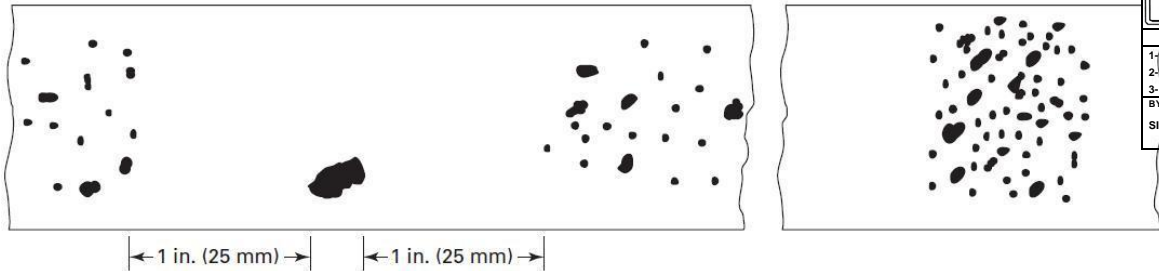

(b) Isolated Indication (c) Cluster

**Figure A-250.3.6-5.** Charts for  $t$  over 50 mm to 100 mm, inclusive



NARGAN COMPANY	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: <i>M. Rezaei</i>	

### 5.3 Acceptance criteria

Density within the image of the indication may vary and is not a criterion for acceptance or rejection.

Indications shown on radiographs of welds and characterized as imperfections are unacceptable under the following conditions.

- Any indication characterized as a crack or zone of incomplete fusion or penetration.
- Any other elongated indication on the radiograph which has length greater than:
  - 6 mm for  $t \leq 19$  mm.
  - $1/3t$  for  $19 \text{ mm} < t \leq 57$  mm.
  - 19 mm for  $t > 57$  mm.
- Any group of aligned indications that have an aggregate length greater than  $t$  in a length of  $12t$  except when the distance between the successive imperfections exceeds  $6L$  where  $L$  is the length of the longest imperfection in the group.
- Rounded indications in excess of that specified by the acceptance standards given in paragraph 5.1.2 up to 5.2.

	NARGAN COMPANY
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

## 6 ASME BPVC Section VIII Division 1, paragraph UW 51

### 6.1 Evaluation

#### 6.1.1 Maximum size of rounded relevant indications

Only those rounded indications which exceed the following dimensions shall be considered relevant:

1/10t	for $t < 3.0$ mm.
0.4 mm	for $3 \text{ mm} \leq t \leq 6$ mm.
0.8 mm	for $6 \text{ mm} < t \leq 50$ mm.
1.6 mm	for $t > 50$ mm.

The maximum permissible size of any indication shall be  $1/4t$ , or 4 mm, whichever is smaller; except that an isolated indication separated from an adjacent indication by 25 mm or more may be  $1/3t$ , or 6 mm, whichever is less. For  $t$  greater than 50 mm, the maximum permissible size of an isolated indication shall be increased to 10 mm.

#### 6.1.2 Aligned rounded indications

Aligned rounded indications are acceptable when the summation of the diameters of the indications is less than  $t$  in any length of  $12t$ , refer to section 6.1.6 Rounded indication charts.

The length of groups of aligned rounded indications and the spacing between the groups shall meet the requirements of section 6.1.6.

#### 6.1.3 Spacing

The distance between adjacent rounded indications is not a factor in determining acceptance or rejection, except as required for isolated indications or groups of aligned indications.

#### 6.1.4 Weld thickness $t$ less than 3.0 mm

For  $t$  less than 3.0 mm the maximum number of rounded indications shall not exceed 12 in any 150 mm weld length. A proportionally fewer number of indications shall be permitted in welds less than 150 mm in length.

#### 6.1.5 Clustered indications

The illustrations for clustered indications show up to four times as many indications in a local area, as that shown in the illustrations for random indications. The length of an acceptable cluster shall not exceed the lesser of 25 mm or  $2t$ . Where more than one cluster is present, the sum of the lengths of the clusters shall not exceed 25 mm in any 150 mm weld length.

#### 6.1.6 Rounded indication charts


The rounded indications characterized as imperfections shall not exceed that shown in the charts. Figures 4-1 through 4-7 illustrate various types of assorted, randomly dispersed and clustered rounded indications for different weld thicknesses greater than 3.0 mm.

These charts represent the maximum acceptable concentration limits for rounded indications. The charts for each thickness range represent full-scale 150 mm radiographs.

Maximum size of individual rounded indications in the Figures 4-1 up to 4-7 shall be as per section 6.1.1.


The distributions shown are not necessarily the patterns that may appear on the radiograph, but are typical of the concentration and size of indications permitted.

	NARGAN COMPANY
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
ISSUE DATE: 16 Dec 2023	
SIGN:	

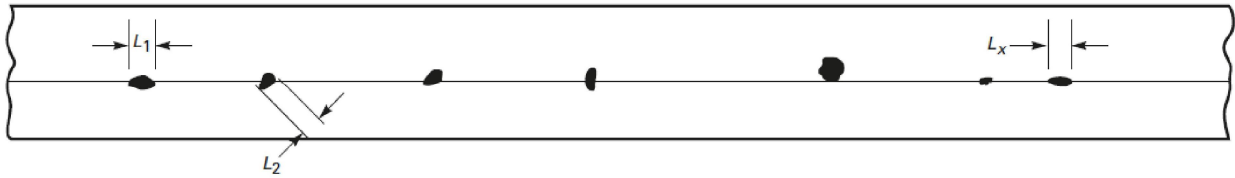

General note: Sum of  $L_1$  to  $L_x$  shall be less than  $t$  in a length of  $12t$ .

**Figure 4-1.** Aligned rounded indications

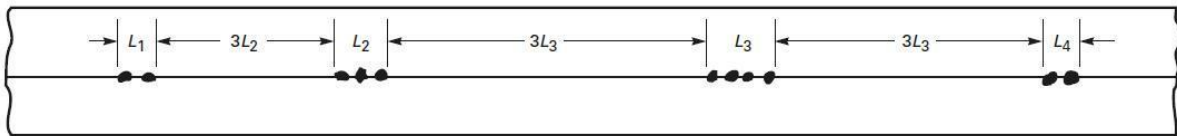

Maximum Group Length


- L = 6 mm for  $t$  less than 19 mm.
- L =  $1/3t$  for  $t$  19 mm to 57 mm.
- L = 19 mm for  $t$  greater than 57 mm.

Minimum Group Spacing


3L where L is the length of the longest adjacent group being evaluated.

General note: Sum of the group lengths shall be less than  $t$  in a length of  $12t$ .

**Figure 4-2.** Groups of aligned rounded indications




(a) Random rounded indications  
 Typical concentration and size permitted in any 150 mm length of weld.

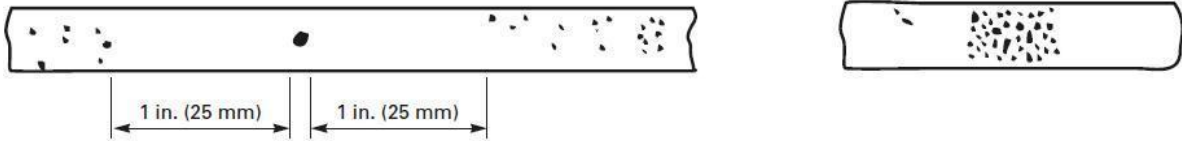


(b) Isolated indications

**Figure 4-3.** Charts for  $t$  equal to 3 mm to 6 mm, inclusive



(a) Random Rounded Indications  
 Typical concentration and size permitted in any 150 mm length of weld.

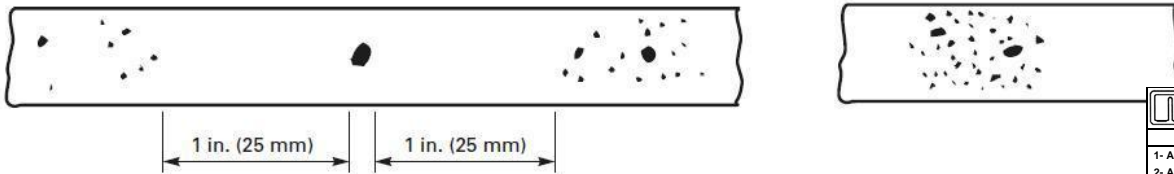


(b) Isolated Indication


(c) Cluster

**Figure 4-4.** Charts for  $t$  over 6 mm to 10 mm, inclusive

NARGAN COMPANY	
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: <i>M. Rezaei</i>	

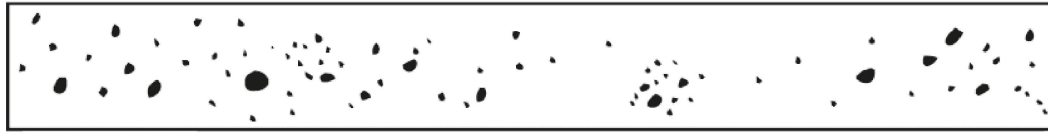


(a) Random Rounded Indications  
 Typical concentration and size permitted in any 150 mm length of weld.

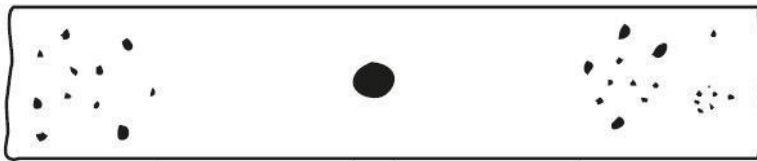

1 in. (25 mm)      1 in. (25 mm)

(b) Isolated Indication

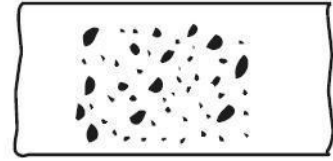


(c) Cluster

**Figure 4-5.** Charts for  $t$  over 10 mm to 19 mm, inclusive




(a) Random Rounded Indications  
 Typical concentration and size permitted in any 150 mm length of weld.

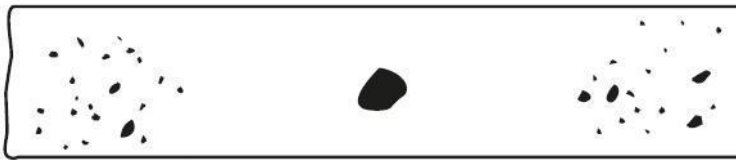

1 in. (25 mm)      1 in. (25 mm)

(b) Isolated Indication

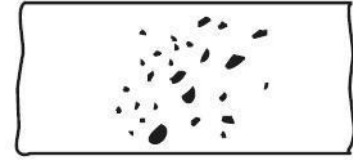

(c) Cluster

**Figure 4-6.** Charts for  $t$  over 19 mm to 50 mm, inclusive

<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN:	





## 7 ASME BPVC Section VIII Division 1, paragraph UW 52

### 7.1 Acceptance criteria

The acceptability of welds examined by spot radiography shall be judged by the following standard.

- Welds in which indications characterised as cracks or zones of incomplete fusion or penetration shall be unacceptable.
- Welds having indications characterized as slag inclusions or cavities are unacceptable when the indication length exceeds  $2/3t$ . For all thicknesses, indications less than 6 mm are acceptable, and indications greater than 19 mm are unacceptable.
- Multiple aligned indications meeting these acceptance criteria are acceptable when the sum of their longest dimensions indications does not exceed  $t$  within a length of  $6t$  (or proportionally for radiographs shorter than  $6t$ ), and when the longest length L for each indication is separated by a distance not less than  $3L$  from adjacent indications.
- Rounded indications are not a factor in the acceptability of welds not required to be fully radiographed.

	NARGAN COMPANY
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

## 8 ASME BPVC Section VIII Division 2, paragraph 7.5.3.2

### 8.1 Evaluation

#### 8.1.1 Maximum size of rounded relevant indications

Only those rounded indications which exceed the following dimensions shall be considered relevant:

1/10t	for $t < 3.0$ mm.
0.4 mm	for $3 \text{ mm} \leq t \leq 6$ mm.
0.8 mm	for $6 \text{ mm} < t \leq 50$ mm.
1.5 mm	for $t > 50$ mm.

### 8.2 Acceptance criteria

#### 8.2.1 Aligned rounded indications

Aligned rounded indications are acceptable when the summation of the diameters of the indications is less than  $t$  in any length of  $12t$ .

#### 8.2.2 Spacing

The distance between adjacent rounded indications is not a factor in determining acceptance or rejection, except as required for isolated indications or groups of aligned indications.

#### 8.2.3 Weld thickness $t$ less than 3.0 mm

For  $t$  less than 3.0 mm the maximum number of rounded indications shall not exceed 12 in every 150 mm weld length. A proportionally fewer number of indications shall be permitted in welds less than 150 mm in length.

#### 8.2.4 Clustered indications

The illustrations for clustered indications show up to four times as many indications in a local area, as that shown in the illustrations for random indications. The length of an acceptable cluster shall not exceed the lesser of 25 mm or  $2t$ . Where more than one cluster present, the sum of the lengths of the clusters shall not exceed 25 mm in any 150 mm weld length.

### 8.3 Rounded indication charts


The rounded indications characterized as imperfections shall not exceed that shown in the charts. The Figures 7-3 up to 7-9 illustrate various types of assorted, randomly dispersed and clustered rounded indications for different weld thicknesses greater than 3.0 mm.

These charts represent the maximum acceptable concentration limits for rounded indications. The charts for each thickness range represent full-scale 150 mm radiographs.

Maximum size of individual rounded indications in the Figures 7-3 up to 7-9 shall be as per section 8.1.1.


The distributions shown are not necessarily the patterns that may appear on the radiograph, but are typical of the concentration and size of indications permitted.

NARGAN COMPANY	
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI	DATE: 16 Dec 2023
SIGN:	

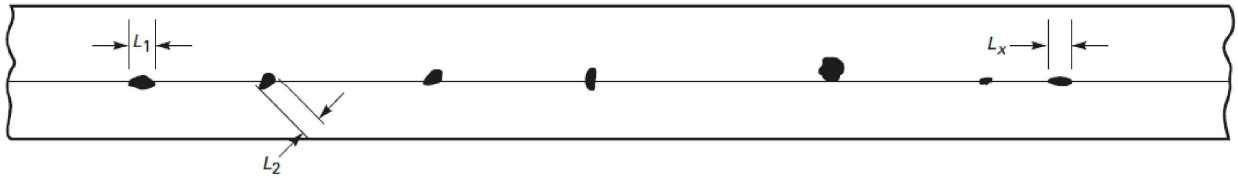

General note: Sum of  $L_1$  to  $L_x$  shall be less than  $t$  in a length of  $12t$ .

**Figure 7-3.** Aligned rounded indications

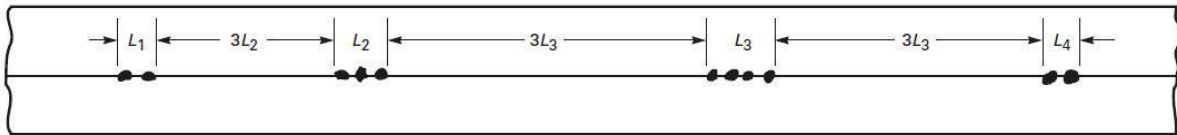


Maximum Group Length	
L	= 6 mm for $t$ less than 19 mm.
L	= $1/3t$ for $t$ 19 mm to 57 mm.
L	= 19 mm for $t$ greater than 57 mm.


Minimum Group Spacing	
	3L where L is the length of the longest adjacent group being evaluated.

General note: Sum of the group lengths shall be less than  $t$  in a length of  $12t$ .

**Figure 7-4.** Groups of aligned rounded indications




(c) Random rounded indications  
 Typical concentration and size permitted in any 150 mm length of weld.



(d) Isolated indications


**Figure 7-5.** Charts for  $t$  equal to 3 mm to 6 mm, inclusive



(a) Random Rounded Indications  
 Typical concentration and size permitted in any 150 mm length of weld.




(b) Isolated Indication




(c) Cluster

**Figure 7-6.** Charts for  $t$  over 6 mm to 10 mm, inclusive

NARGAN COMPANY	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN:	

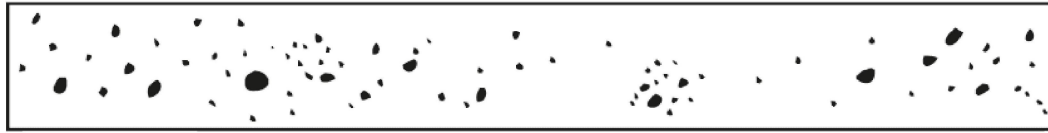


(a) Random Rounded Indications  
 Typical concentration and size permitted in any 150 mm length of weld.

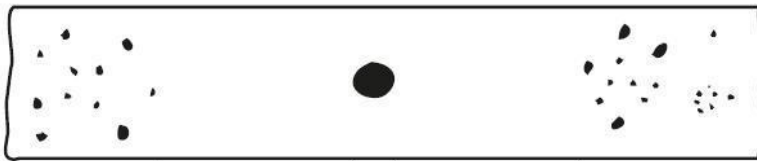

1 in. (25 mm)      1 in. (25 mm)

(b) Isolated Indication

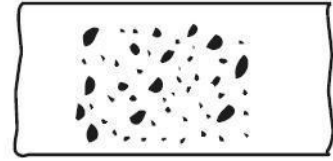


(c) Cluster

**Figure 7-7.** Charts for  $t$  over 10 mm to 19 mm, inclusive




(a) Random Rounded Indications  
 Typical concentration and size permitted in any 150 mm length of weld.

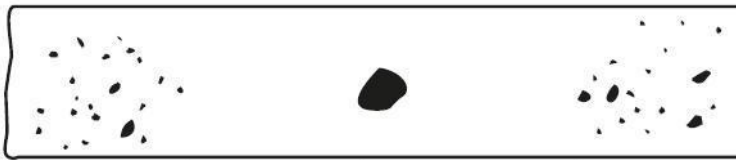

1 in. (25 mm)      1 in. (25 mm)


(b) Isolated Indication

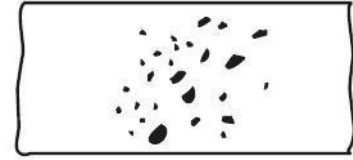


(c) Cluster

**Figure 7-8.** Charts for  $t$  over 19 mm to 50 mm, inclusive

<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN:	

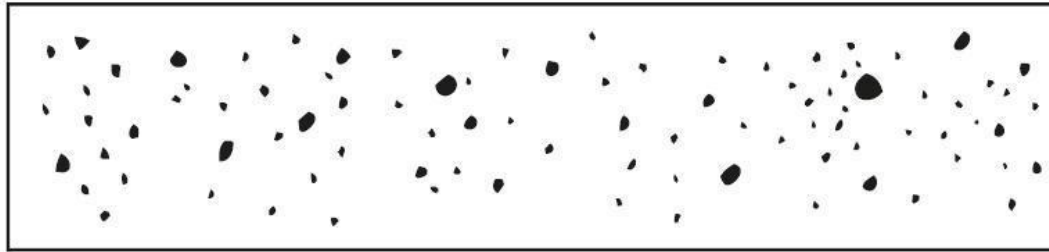

(a) Random Rounded Indications  
Typical concentration and size permitted in any 150 mm length of weld.

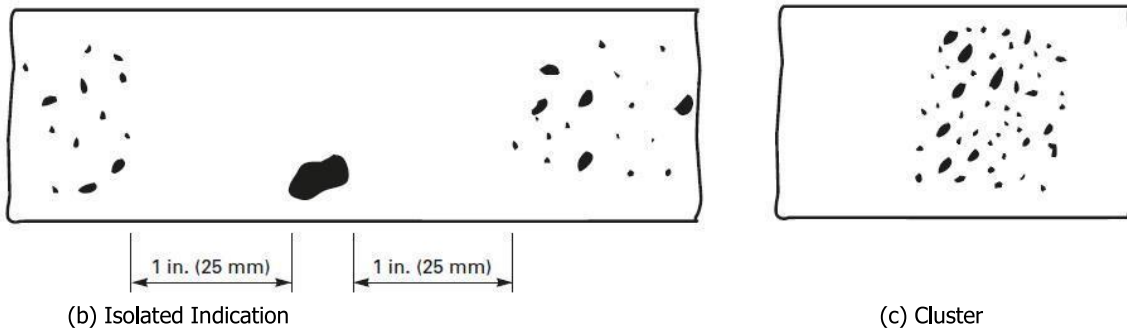

(b) Isolated Indication

(c) Cluster

**Figure 7-9.** Charts for  $t$  over 50 mm to 100 mm, inclusive

Indications shown on radiographs of welds and characterized as imperfections are unacceptable under the following conditions.

- Any indication characterized as a crack or zone of incomplete fusion or penetration.
- Any other elongated indication on the radiograph which has length greater than:
  - 6 mm for  $t \leq 19$  mm.
  - $1/3t$  for  $19 \text{ mm} \leq t \leq 57$  mm.
  - 19 mm for  $t > 57$  mm.
- Any group of aligned indications that have an aggregate length greater than  $t$  in a length of  $12t$  except when the distance between the successive imperfections exceeds  $6L$  where  $L$  is the length of the longest imperfection in the group.
- Internal root conditions are acceptable when the density or image brightness change as indicated in the radiograph is not abrupt. Linear indication on the radiograph at either edge of such conditions shall be evaluated with bullet above.
- Rounded indications in excess of that specified by the acceptance standards given below.

The maximum permissible size of any indication shall be  $1/4t$ , or 4 mm, whichever is smaller; except that an isolated indication separated from an adjacent indication by 25 mm or more may be  $1/3t$ , or 6 mm, whichever is less. For  $t$  greater than 50 mm, the maximum permissible size of an isolated indication shall be increased to 10 mm.

<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN:	

## 9 ASME BPVC Section IX, paragraph QW 191.1.2

### 9.1 Acceptance Criteria

Welder and welding operator performance test by radiography of welds in test assemblies shall be judged unacceptable when the radiograph exhibits any imperfections in excess of the limits specified below.

#### 9.1.1 Linear indications


- Any type of crack or zone of incomplete fusion or penetration.
- Any elongated slag inclusion which has a length greater than:
  - 3 mm for  $t \leq 10$  mm.
  - $1/3t$  for  $10 \text{ mm} < t \leq 57$  mm.
  - 19 mm for  $t > 57$  mm.
- Any group or slag inclusion in line that have an aggregate length greater than  $t$  in a length of  $12t$ , except when the distance between the successive imperfections exceeds  $6L$  where  $L$  is the length of the longest imperfection in the group.

#### 9.1.2 Rounded indications


- The maximum permissible dimension for rounded indications shall be 20% of  $t$  or 3 mm, whichever is smaller.
- For welds in material less than 3 mm in thickness, the maximum number of acceptable rounded indications shall not exceed 12 in a 150 mm length of weld. A proportionally fewer number of rounded indications shall be permitted in welds less than 150 mm in length.
- For welds in material 3 mm or greater in thickness, the charts in section 9.2 represent the maximum acceptable type of rounded indications illustrated in typically clustered, assorted and randomly dispersed configurations. Rounded indications less than 0.8 mm in maximum diameter shall not be considered in the radiographic acceptance tests of welders and welding operators in these ranges of material thicknesses.

### 9.2 Rounded indication chart


These charts represent the maximum acceptable concentration limits for rounded indications. The charts for each thickness range represent full-scale 150 mm radiographs.




Typical quantity and size permitted in 150 mm length of weld 3 mm to 6 mm thickness.



Typical quantity and size permitted in 150 mm length of weld over 6 mm to 13 mm thickness.

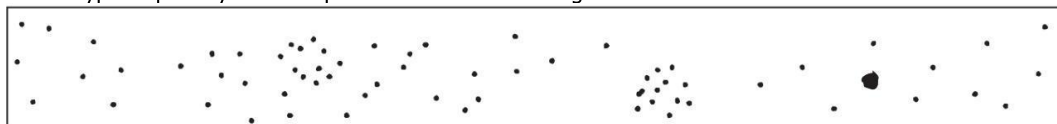

Typical quantity and size permitted in 150 mm length of weld over 3 mm to 25 mm thickness.

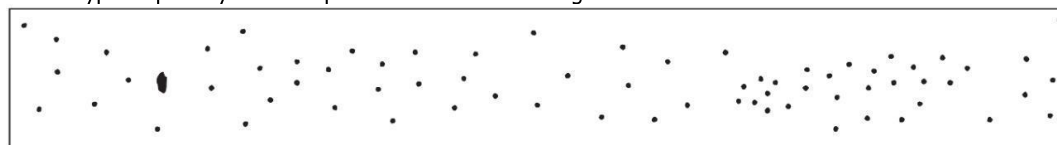

Typical quantity and size permitted in 150 mm length of weld over 25 mm.

**Figure QW-191.1.2.2(b)(4)** Rounded indication charts

<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAIE DATE: 16 Dec 2023	
SIGN:	

## 10 ASME B31.1, paragraph 136.4.5

### 10.1 Acceptance criteria linear indications

Indications shown on radiographs of welds and characterized as imperfections are unacceptable under the following conditions:

Any type of crack or zone of incomplete fusion or penetration.

Any other elongated indication that has a length greater than:

- 6.0 mm for  $t \leq 19.0$  mm.
- $1/3t$  for  $19.0 \text{ mm} < t \leq 57.0$  mm.
- 19.0 mm for  $t > 57.0$  mm.



If a weld joins two members having different thickness at the weld,  $t$  is the thinner of these two thicknesses.

Any group of indications in line that have an aggregate length greater than  $t$  in a length of  $12t$ , except where the distance between the successive indications exceeds  $6L$  where  $L$  is the longest indication in the group.

Root concavity when there is an abrupt change in density, as indicated on the radiograph.

### 10.2 Acceptance criteria for rounded indications

Porosity in excess of that shown as acceptable in non-mandatory appendix A, A-250 of ASME BPVC section I, refer to section 5.1.1 up to 5.3 of this procedure.

	NARGAN COMPANY
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

## 11 ASME B31.3, table 341.3.2

Indications shown on radiographs of welds and characterized as imperfections are unacceptable under the following conditions as stated into, table 341.3.2 (as shown in section 11.2) for the service conditions discussed.


If no service condition is given the "Severe Cyclic Condition" shall be used.

### 11.1 Acceptance criteria for rounded indications

The acceptance criteria for rounded indications shall be as per Table 341.3.2, symbol D and E,(refer to section 11.2) and to the ASME BPVC, section VIII, Division 1, Appendix 4 as described in section 6.1.1 through 6.2 of this procedure.

#### 11.1.1 Image density

Density within the image of the indication may vary and is not a criterion for acceptance or rejection.

	NARGAN COMPANY
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M.REZAEI DATE: 16-Dec-2023	
SIGN: 	

### 11.2 Table 341.3.2 Acceptance criteria for welds

**Table 341.3.2 Acceptance Criteria for Welds — Visual and Radiographic Examination**


Criteria (A to M) for Types of Welds and for Service Conditions [Note (1)]										Examination Methods	
Normal and Category M Fluid Service			Severe Cyclic Conditions				Category D Fluid Service			Visual	Radiography
Girth, Miter Groove, and Branch Connection Welds [Note (2)]	Longitudinal Groove Weld [Note (3)]	Fillet Weld [Note (4)]	Girth, Miter Groove, and Branch Connection Welds [Note (2)]	Longitudinal Groove Weld [Note (3)]	Fillet Weld [Note (4)]	Girth and Miter Groove Welds [Note (4)]	Longitudinal Groove Weld [Note (3)]	Fillet Weld [Note (4)]	Branch Connection Weld [Note (2)]	Weld Imperfection	
A	A	A	A	A	A	A	A	A	A	Crack	✓
A	A	A	A	A	A	C	A	N/A	A	Lack of fusion	✓
B	A	N/A	A	A	N/A	C	A	N/A	B	Incomplete penetration	✓
E	N/A	N/A	D	D	N/A	N/A	N/A	N/A	N/A	Rounded Indications	✓
G	N/A	N/A	F	F	N/A	N/A	N/A	N/A	N/A	Linear indications	✓
H	A	H	A	A	A	I	A	H	H	Undercutting	✓
A	A	A	A	A	A	A	A	A	A	Surface porosity or exposed slag inclusion [Note (5)]	✓
N/A	N/A	N/A	J	J	J	N/A	N/A	N/A	N/A	Surface finish	✓
K	K	N/A	K	K	N/A	K	K	N/A	K	Concave surface, concave root, or burn-through	✓
L	L	L	L	L	L	M	M	M	M	Weld reinforcement or internal protrusion	✓

**GENERAL NOTES:**

- (a) Weld imperfections are evaluated by one or more of the types of examination methods given, as specified in paras. 341.4.1, 341.4.2, 341.4.3, and M341.4, or by the engineering design.
- (b) "N/A" indicates the Code does not establish acceptance criteria or does not require evaluation of this kind of imperfection for this type of weld.
- (c) Check (✓) indicates examination method generally used for evaluating this kind of weld imperfection.
- (d) Ellipsis (...) indicates examination method not generally used for evaluating this kind of weld imperfection.

**NOTES:**

- (1) Criteria given are for required examination. More-stringent criteria may be specified in the engineering design. See also paras. 341.5 and 341.5.3.
- (2) Branch connection weld includes pressure containing welds in branches and fabricated laps.
- (3) Longitudinal groove weld includes straight and spiral (helical) seam. Criteria are not intended to apply to welds made in accordance with a standard listed in Table A-1, Table A-1M, or Table 326.1. Alternative Leak Test requires examination of these welds; see para. 345.9.
- (4) Fillet weld includes socket and seal welds, and attachment welds for slip-on flanges, branch reinforcement, and supports.
- (5) These imperfections are evaluated only for welds ≤5 mm (3/16 in.) in nominal thickness.



Criterion Value Notes for Table 341.3.2

Symbol	Criterion	Measure	Acceptable Value Limits [Note (1)]
A	Extent of imperfection		Zero (no evident imperfection)
B	Cumulative length of incomplete penetration		≤38 mm (1.5 in.) in any 150 mm (6 in.) weld length or 25% of total weld length, whichever is less
C	Cumulative length of lack of fusion and incomplete penetration		≤38 mm (1.5 in.) in any 150 mm (6 in.) weld length or 25% of total weld length, whichever is less
D	Size and distribution of rounded indications		See ASME BPVC, Section VIII, Division 1, Appendix 4 [Note (2)]
E	Size and distribution of rounded indications		For $\bar{T}_{w} \leq 6$ mm ( $1/4$ in.), limit is same as D [Note (2)] For $\bar{T}_{w} > 6$ mm ( $1/4$ in.), limit is $1.5 \times D$ [Note (2)]
F	Linear indications		$\leq \bar{T}_{w}/3$
	Individual length		$\leq 2.5$ mm ( $3/32$ in.) and $\leq \bar{T}_{w}/3$
	Individual width		$\leq \bar{T}_{w}$ in any 12 $\bar{T}_{w}$ weld length [Note (2)]
G	Cumulative length		$\leq 2\bar{T}_{w}$
	Linear indications		$\leq 3$ mm ( $1/8$ in.) and $\leq \bar{T}_{w}/2$
	Individual length		$\leq 4\bar{T}_{w}$ in any 150 mm (6 in.) weld length [Note (2)]
	Individual width		$\leq 1$ mm ( $1/32$ in.) and $\leq \bar{T}_{w}/4$
H	Cumulative length		$\leq 38$ mm (1.5 in.) in any 150 mm (6 in.) weld length or 25% of total weld length, whichever is less
	Depth of undercut		$\leq 1.5$ mm ( $1/16$ in.) and $\leq \bar{T}_{w}/4$ or 1 mm ( $1/32$ in.)
I	Depth of undercut		$\leq 38$ mm (1.5 in.) in any 150 mm (6 in.) weld length or 25% of total weld length, whichever is less
	Cumulative length of internal and external undercut		$\leq 38$ mm (1.5 in.) in any 150 mm (6 in.) weld length or 25% of total weld length, whichever is less
J	Surface roughness		$\leq 12.5$ $\mu\text{m}$ (500 $\mu\text{in.}$ ) $R_a$ in accordance with ASME B46.1
K	Depth of surface concavity, root concavity, or burn-through		Total joint thickness, including weld reinforcement, $\geq \bar{T}_{w}$ [Notes (3) and (4)]
L	Height of reinforcement or internal protrusion [Note (5)] in any plane through the weld shall be within limits of the applicable height value in the tabulation at right, except as provided in Note (6). Weld metal shall merge smoothly into the component surfaces.		For $\bar{T}_{w}$ mm (in.) $\leq 6$ ( $1/4$ ) $> 6$ ( $1/4$ ), $\leq 13$ ( $1/2$ ) $> 13$ ( $1/2$ ), $\leq 25$ (1) $> 25$ (1) Limit is twice the value applicable for L above
M	Height of reinforcement or internal protrusion [Note (5)] as described in L. Note (6) does not apply.		Height, mm (in.) $\leq 1.5$ ( $1/16$ ) $\leq 3$ ( $1/8$ ) $\leq 4$ ( $3/32$ ) $\leq 5$ ( $3/16$ )

NOTES:

(1) Where two limiting values are separated by "and," the lesser of the values determines acceptance. Where two sets of values are separated by "or," the larger value is acceptable.  $\bar{T}_{w}$  is the nominal wall thickness of the component.

(2) Where two sets of values are separated by "and," the lesser of the values determines acceptance. Where two sets of values are separated by "or," the larger value is acceptable.  $\bar{T}_{w}$  is the nominal wall thickness of the component.

INSPECTION	
1. APPROVED	<input type="checkbox"/>
2. APPROVED AS NOTED	<input checked="" type="checkbox"/>
3. NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2021	
SIGN:	

**Criterion Value Notes for Table 341.3.2 (Cont'd)**

NOTES: (Cont'd)

- (2) Porosity and inclusions such as slag or tungsten are defined as rounded indications where the maximum length is three times the width or less. These indications may be circular, elliptical, or irregular in shape; may have tails; and may vary in density. Indications where the length is greater than three times the width are defined as linear indications and may also be slag, porosity, or tungsten.
- (3) For circumferential groove welded joints in pipe, tube, and headers made entirely without the addition of filler metal, external concavity shall not exceed the lesser of 1 mm ( $1/32$  in.) or 10% of the joint nominal thickness. The contour of the concavity shall blend smoothly with the base metal. The total joint thickness, including any reinforcement, shall not be less than the minimum wall thickness,  $t_n$ .
- (4) For radiography, acceptability may be determined by comparing the density of the image through the affected area to the density through the adjacent base metal ( $\bar{T}_p$ ). If digital radiography is used, brightness comparison may be utilized. A density or brightness darker than the adjacent base metal is cause for rejection.
- (5) For groove welds, height is the lesser of the measurements made from the surfaces of the adjacent components; both reinforcement and internal protrusion are permitted in a weld. For fillet welds, height is measured from the theoretical throat, Figure 328.5.2A; internal protrusion does not apply.
- (6) For welds in aluminum alloy only, internal protrusion shall not exceed the following values:
  - (a) 1.5 mm ( $1/16$  in.) for thickness  $\leq 2$  mm ( $3/64$  in.)
  - (b) 2.5 mm ( $3/32$  in.) for thickness  $> 2$  mm and  $\leq 6$  mm ( $1/4$  in.)
For external reinforcement and for greater thicknesses, see the tabulation for symbol L.

<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN:	

# CERTIFICAAT

nummer / number  
**N 43899**

**Stichting Hobéon SKO Certificatie**  
te Den Haag

verklaart dat  
certifies that

***V.M.J. Spieringhs***  
(Hobéon SKO nr: 108113)

geboren **05 maart 1982**  
date of birth

te **Bergen op Zoom**  
at

voldoet aan de certificatie-eisen conform de Hobéon SKO-regelingen voor het systeem SKNDO versie 7  
*meets the certification criteria of the the Hobéon SKO regulations for the SKNDO system version 7*

**Radiografisch onderzoek (niveau 3) volgens ISO 9712:2012**  
***Radiographic testing (level 3) in accordance with ISO 9712:2012***

voor de sector Beproeving vóór en tijdens gebruik, incl. fabricage  
*for the sector Pre- and in-service testing which includes manufacturing*


De examenprocedure en -eisen zijn overeenkomstig ISO 9712  
*The examination procedure en requirements are in accordance with ISO 9712*

Dit certificaat is tevens een bewijs van goedkeuring voor het uitvoeren van niet-destructief onderzoek in de genoemde methode en niveau op permanente verbindingen voor drukapparatuur van de categorieën III en IV in overeenstemming met de Europese Richtlijn voor Drukapparatuur 2014/68/EU bijlage I artikel 3.1.3 (PED).

*This Certificate is evidence of approval to carry out non-destructive tests in the method and level mentioned on permanent joints for pressure equipment in categories III and IV in accordance with European Pressure Equipment Directive 2014/68/EU Annex 1, section 3.1.3 (PED).*

Dit certificaat is geldig vanaf **01 december 2017**  
*This certificate is valid from*


tot **01 december 2022**  
*until*



drs. B. Verstegen  
namens het bestuur  
*on behalf of the board*



Handtekening certificaathouder  
*Signature certificate holder*

NARGAN COMPANY	
INSPECTION	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAIEI DATE: 16 Dec 2022	
SIGN: 	

Kopieën zijn alleen geldig, indien voorzien van originele handtekeningen van door het bestuur geautoriseerde personen. Dit certificaat is eigendom van Hobéon SKO.  
*Copies are valid only, if provided with original signatures of persons authorized by the board. This certificate is the property of Hobéon SKO.*

## SOP 30-01 FERRITE MEASUREMENT (INDUCTIVE METHOD)

### 1 APPLICATION AREA

- 1.1.1 This work instruction describes the method that can be used to determine the ferrite content of austenitic metals semi-quantitatively (Förster or Permascope), and austenitic metals and duplex ferritic/austenitic metals quantitatively (Feritscope).
- 1.1.2 The testing procedures described in this document are implemented at the Element locations mentioned in the RvA and Belac scope.
- 1.1.3 As different types of ferrite meters are used within the enterprise, the various subsections describe the instrument's specific practices.
- 1.1.4 The activities described can also be carried out at other locations:
- On site on the client's premises or at a location designated by the client.

### 2 PRINCIPLE

- 2.1.1 An alternating magnetic field is imposed on the test object by placing a probe on the surface to be measured. The intensity of the magnetic field at that position is the result of interaction of the imposed magnetic field with the test object. The strength of the interaction depends on the magnetic properties of the object's material and is therewith a measure for the ferrite "content". The resulting magnetic signal is registered by the probe and converted to ferrite values by the ferrite meter.

### 3 DEFINITIONS AND REFERENCES

#### 3.1 Definitions

- 3.1.1 As specified in applicable documents.

#### 3.2 References


- a. SP 706, "Handling of Test Items".
- b. SP 708, "Reporting Results".
- c. Element Materials Technology Safety, Health and Environment (SHE) Company Policy Statement.
- d. BP 5109, "Personal Protective Equipment".
- e. BP 5119, "Stop Work Authority".
- f. Instruction manuals of equipment to be used or specified instruction.

### 4 PERSONNEL

- 4.1.1 The specified activities may only be carried out by employees with the required training and experience in the setup and the use of the equipment as well as in the correct evaluation of the results. The competence of personnel is to be evaluated by the departmental manager, and is laid down in the list of qualifications.

### 5 EQUIPMENT AND MATERIALS

- 5.1.1 In order to perform the work described, use is made of equipment that is laid down in the equipment file of the respective department.
- 5.1.2 For this work instruction, specific use is made of the following equipment:
- a. Ferrite content meters from Institut Dr. Förster, type 1.053.
  - b. Feritscope MP3, MP30 and FMP30 from Fischer.

NARGAN COMPANY	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

c. Permascope ES from Fischer.

5.1.3 The Permascope and the Förster are only to be used for the (semi-quantitative) determination of low ferrite contents (up to 15%), as can be found in austenitic stainless steels (for example 316, 304)

5.1.4 The Ferritscope can be used for either low or high ferritic material (including duplex stainless steels)

## 6 REQUIREMENTS

### 6.1 Förster, Feritscope, Permascope

6.1.1 The ferrite content meter and in particular the feeler must be handled with great care. The following requirements must be observed in order to get a good and reliable measurement:

- a. Keep magnets away from the probe.
- b. Do not use the device near strong magnetic fields.
- c. The adjusting blocks must be kept completely away from magnetic fields. If there is doubt about the presence of magnetic fields, a check must be performed using a residual field indicator.
- d. Check that the equipment includes a screwdriver (Förster and Permascope).

## 7 CALIBRATIONS/VERIFICATIONS

7.1.1 Before a measurement is taken, the device must first be calibrated according to the instrument manual.

## 8 PREPARATION

8.1.1 Test specimen shall be in accordance with **SP 706**.

### 8.2 Förster, Feritscope, Permascope

8.2.1 The surface of the test piece to be measured must be stripped of all surface layers that may affect the results of the analysis (unless the analysis specifically relates to these layers).

8.2.2 Impurities such as grease etc. are to be removed.

8.2.3 For the most accurate measurements the surface to be analyzed shall be sanded flat (to grain 120 or finer).

8.2.4 In many cases (like on welds, tubing, fittings etc.) excessive sanding may not be possible, or may not be allowed or simply not desirable by the client. In those cases, always be critical with respect to the registered ferrite values. Pay special attention to:

- possible influence of a convex, concave or irregular surface,
- possible influence of edge effects.

## 9 SETTING EQUIPMENT



### 9.1 Förster

9.1.1 The ferrite content meter must first be set before measurements can be taken.

9.1.2 The meter includes a set of 5 adjusting blocks. An adjusting block is chosen according to the scale selected.

9.1.3 The setting procedure is as follows:

- a. Clean the probe and connect it to the meter.
- b. Check the condition of the batteries of the meter using the "Batt. check" position.

	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI	DATE: 16 Dec 2023
SIGN:	

- c. Check the mechanical zero point:
  - Set the **mechanical** selector switch to OPERATION and the range switch to 0.
  - Correct the zero indication with a screwdriver, if necessary.
- d. Checking the electrical zero point:
  - Set range switch to 12 (the most used position).
  - While checking the **electrical** zero point, the probe must be moved through the air. Adjust the **electrical** zero point if necessary using the fine control button and/or step switch (positions 1–12) on the compensator (COMP). If the earth field does not seem to be homogeneous during this check measurement, measurements cannot be performed on a more sensitive scale.

## 9.2 Feritscope

- 9.2.1 The instrument can be set for ferrite % or ferrite number. The instructions for this are given in the manual.
- 9.2.2 Keep in mind that the requirements for the ferrite content can be given in either "**%-ferrite**" or in other cases as a "**ferritenumber**" (FN or EFN). Make sure that the right units are used and reported. And use the correct calibration values for % or FN.
- 9.2.3 For a possible conversion of the measured % ferrite to a ferrite number (or vice versa), the applicable conversion factor depends on the material type. In this case the Group Leader should be consulted.
- 9.2.4 The measuring zone will be calibrated with 3 calibration samples with the closest values from the set of 5 (+1 basic sample) supplied.



## 9.3 Permascope

- 9.3.1 The instrument is set for ferrite %.
- 9.3.2 The setting procedure is as follows:
  - a. Clean the probe and connect it **to the meter**.
  - b. Connect the 240V cable **to the meter**.
  - c. Check the mechanical zero point:
    - Set **the** selector switch to ON and the range switch to 0.
    - Correct the **mechanical** zero indication with a screwdriver, if necessary.
  - d. Check the electrical zero point:
    - o Set range switch to II (the range 0 – 20% ).
    - o While checking the **electrical** zero point, the probe must be moved through the air. Adjust the **electrical** zero point if necessary using the ZERO CONTROL knob. If the earth field does not seem to be stable during this check measurement, measurements cannot be performed on the more sensitive scale (scale I)
  - e. Adjust the SENSITIVITY while measuring the adjusting block with a value closest to the expected values on the test sample.

## 10 PERFORMING THE TEST

### 10.1 Förster

- 10.1.1 Adjust the degree of accuracy of the meter to the ferrite content of the material to be examined, starting with the scale 0–12% ferrite. Check the meter display with the adjusting block belonging to the working range; always look up the highest value for each block (adjust using GAIN if the meter deviates from the value of the adjusting block by more than  $\pm 0.2\%$  in absolute terms).
- 10.1.2 No adjusting block is present for the most sensitive position of the device (position 1). The adjusting block with a ferrite content of 1.08% can be used to check whether the pointer clearance comes out at above the ferrite content of 1% in each case in this position. The measurements on the most sensitive scale are therefore only indicative values.

 NARGAN COMPANY	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

- 10.1.3 Once the measurements have been taken:
- Disconnect the probe.
  - Switch off the meter.
  - The device must be put away carefully

## 10.2 *Feritscope*

- 10.2.1 The instrument can be used for measuring weld metals as well as base metals.
- 10.2.2 When measuring the surface of rolled material, deviations can occur as a result of oriented micro-structure.
- 10.2.3 A convex surface may lead to display too low values, whereas a concave surface can result in the display of too high ferrite values.
- 10.2.4 The surface which is to be measured needs to be of sufficient size to be able to avoid measurements within 3 mm of the edge of the object.
- 10.2.5 Edge effects will cause a display of too low ferrite values (ferrite number or ferrite content).
- 10.2.6 The instrument can be used for materials with both low and high ferrite contents (including duplex stainless steels)
- 10.2.7 Keep the probe as near as perpendicular to the surface as possible, and make sure that a good contact between the probe and the surface is present.
- 10.2.8 Check the correct operation of the selected ferrite meter by means of the verification samples before a measurement series is started (at least once a day). The values found during this verification shall not deviate more than 5% relative from the applicable values on the respective verification plates. When the deviation exceeds 5% relative, the meter is to be adjusted prior to the measurements.
- 10.2.9 The results of the verification measurements are documented on the observations sheet. It shall be indicated if the measurements have been preceded by a recalibration.
- 10.2.10 On the object or location to be tested, at least three measurements are to be performed at the surface. If the tested object is expected to be more or less homogeneous\*), one or more measurements are added to the set of three measurements in case the standard deviation of the three measurements exceeds 5% relative. During calculation of the average value, the most extreme value (or in case more than 5 measurements are performed: if necessary the two most extreme values) is (are) not taken into account.
- \*) **NB:** During measurements on inhomogeneous material, such as weld material, a larger variation in the results will most likely occur. In this case it may be decided to report the highest and lowest value per separate location.


## 10.3 *Permascope*

- 10.3.1 Only use the instrument for measuring low ferrite contents up to max. 15%, as in the case of austenitic stainless steel grades (SS 316, SS 304).

## 11 RECORDING THE MEASUREMENT DATA

### 11.1 *Förster, Feritscope, Permascope*

- 11.1.1 The raw measurement data are recorded in the relevant document.

	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

## 12 MEASUREMENT UNCERTAINTY

### 12.1 Förster

- 12.1.1 Due to the complex and indirect nature of this measurement, it is not possible to determine the measurement uncertainty with the standard method. Measured values shall be considered semi-quantitative. Measurement uncertainty can be as high as 20% relative.
- 12.1.2 As indicated above, measurements are taken after calibration of the instrument with verification samples. If there is any doubt, it is recommended that the results are verified with a metallographic method of Manual Point Count as described in SOP 30-02.

### 12.2 Feritscope

- 12.2.1 Inter laboratory tests have indicated that an reproducibility of within around 1.6% absolute can be attained on perfectly prepared duplex stainless steel samples containing approx. 50% ferrite (i.e. approx. 3% relative), while the results were in good agreement, and within the validity range, of the results of Manual Point Counting (see SOP 30.02) on the same samples.
- Thus the uncertainty of measurement on prepared samples can be compared with those of Manual Point Counting.
- In practice however, especially with on-site measurements on welds, the measured values shall be considered semi- quantitative.

### 12.3 Permascope

- 12.3.1 Measured values shall be considered semi-quantitative. Measurement uncertainty is estimated to be as high as 20% relative.

## 13 REPORTING OF THE RESULTS

### 13.1 Approval and rejection criteria


- 13.1.1 The approval and rejection criteria depend on the type of material and the corresponding material specification(s). The material specification(s) must be submitted by the client.
- 13.1.2 Deviations from the specification will be indicated in the report and, on requests of the client, a comment regarding their relevance may be added.
- 13.1.3 The Measurement Uncertainty section is also important in this respect.
- 13.1.4 Material approval or rejection is the exclusive right of the client.

### 13.2 Report

- 13.2.1 The test results have to be reported in accordance with system procedure **SP 708**.
- 13.2.2 If the applicable standards and/or the client have specified any additional requirements regarding the test report, these shall be met.

- 13.2.3 For the current operation, the report shall include the following data:

- a. Identification of the test piece(s).
- b. Indication of the equipment used and the registration number.
- c. Reference to the ferrite measuring method used.
- d. Units used (%-ferrite or FN) (only for feritscope)
- e. The working range used (if applicable).
- f. Percentage of measured items (if applicable).
- g. The results obtained.
- h. Description of any circumstances that may have affected the results

	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 	

- (if applicable).
- i. The applicable material specification as far as known and relevant.
- j. Note referring to the semi-quantitative nature of the measurements (only for ferritscope)
- k. Explanation of the semi-quantitative nature of the measurements only for Förster and perma-scope)

**14 SAFETY MEASURES**

- 14.1.1 No special safety measures are required for this test.
- 14.1.2 If ferrite measurements are carried out on site at the client's premises or at a location designated by the client, then the client is responsible for adequate safety measures being taken at those locations.

**15 ANNEXES**

None.

**16 RECORD OF FIRST EDITION**


First edition	Drafted by	Approved by	Date
00	P.J. Kuijper	R. Lenferink	31-01-2017

**17 PERIODIC ASSESSMENT**

--

**18 SUMMARY OF AMENDMENTS**

Revision	Description	Performed by	Date
01	<ul style="list-style-type: none"> <li>• New Element Logo</li> <li>• Removed test locations</li> <li>• Added test standards</li> <li>• Renaming SP's</li> <li>• Some editorial changes</li> </ul>	R. Lenferink	01-09-2019

 <b>NARGAN COMPANY</b>	
<b>INSPECTION</b>	
1- APPROVED	<input type="checkbox"/>
2- APPROVED AS NOTED	<input checked="" type="checkbox"/>
3- NOT APPROVED	<input type="checkbox"/>
BY: M. REZAEI DATE: 16 Dec 2023	
SIGN: 